



UNIVERSITÀ
DEGLI STUDI
FIRENZE

FLORE

Repository istituzionale dell'Università degli Studi di Firenze

Olive oil-based method for the extraction, quantification and identification of microplastics in soil and compost samples

Questa è la Versione finale referata (Post print/Accepted manuscript) della seguente pubblicazione:

Original Citation:

Olive oil-based method for the extraction, quantification and identification of microplastics in soil and compost samples / Scopetani C.; Chelazzi D.; Mikola J.; Leinio V.; Heikkinen R.; Cincinelli A.; Pellinen J.. - In: SCIENCE OF THE TOTAL ENVIRONMENT. - ISSN 0048-9697. - ELETTRONICO. - 733:(2020), pp. 1-7. [10.1016/j.scitotenv.2020.139338]

Availability:

This version is available at: 2158/1220090 since: 2024-04-29T16:57:00Z

Published version:

DOI: 10.1016/j.scitotenv.2020.139338

Terms of use:

Open Access

La pubblicazione è resa disponibile sotto le norme e i termini della licenza di deposito, secondo quanto stabilito dalla Policy per l'accesso aperto dell'Università degli Studi di Firenze (<https://www.sba.unifi.it/upload/policy-oa-2016-1.pdf>)

Publisher copyright claim:

(Article begins on next page)



Olive oil-based method for the extraction, quantification and identification of microplastics in soil and compost samples

Costanza Scopetani^{a,*}, David Chelazzi^b, Juha Mikola^a, Ville Leiniö^c, Reijo Heikkinen^d,
Alessandra Cincinelli^{b,e}, Jukka Pellinen^a

^a Faculty of Biological and Environmental Sciences, Ecosystems and Environment Research Programme, University of Helsinki, Niemenkatu 73, Lahti FI-15140, Finland

^b Department of Chemistry "Ugo Schiff", University of Florence, and Consorzio Interuniversitario per lo Sviluppo dei Sistemi a Grande Interfase (CSGI), 50019 Sesto Fiorentino, Florence, Italy

^c Muovipoli Oy, Niemenkatu 73, 15140 Lahti, Finland


^d LAB University of Applied Science, Mukkulankatu 19, Lahti 15210, Finland

^e Department of Chemistry "Ugo Schiff", University of Florence, 50019 Sesto Fiorentino, Florence, Italy

HIGHLIGHTS

- A methodology for microplastic extraction from solid samples is suggested.
- Olive oil was selected to extract microplastics from soil and compost samples.
- The developed method is able to extract high density polymers.
- High recovery rate of $90\% \pm 2\%$ to $97\% \pm 5\%$ were achieved.
- Olive oil seems to have high affinity for a wide set of polymers.

GRAPHICAL ABSTRACT

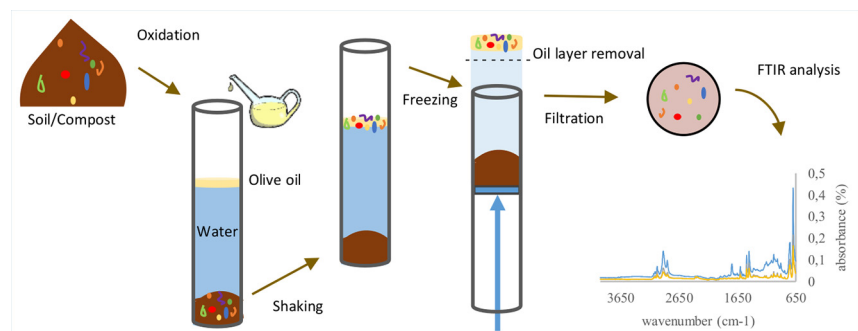

ARTICLE INFO

Article history:

Received 25 March 2020

Received in revised form 7 May 2020

Accepted 8 May 2020

Available online xxxx

Editor: Damia Barcelo

Keywords:

Olive oil

Compost

Recycled fertilizers

Soil

Microplastics extraction

Microplastics quantification

ABSTRACT

Microplastics (MPs) have become a pressing environmental concern over the past few years and their extraction from solid samples is a scientific challenge that needs to be faced and solved.

Standardized and validated protocols for MPs extraction are lacking and the existing methodology, such as density separation, is often unable to separate high density polymers. The aim of our research was to develop a non-density based, inexpensive, simple and safe method to extract MPs from soil and compost samples. We tested an oil-based extracting technique exploiting the oleophilic properties of plastics. For validating the method, soil and compost samples were spiked with six different micro-polymers: polyethylene, polystyrene, polyvinyl chloride, polycarbonate, polyethylene terephthalate and polyurethane. The obtained results are promising, and the polymer density had only a small role in the recovery rate: low, medium and high density polymers reached a mean recovery rate of $90\% \pm 2\%$, $97\% \pm 5\%$ and $95\% \pm 4\%$, respectively.

© 2020 Published by Elsevier B.V.

* Corresponding author.

E-mail address: costanza.scopetani@helsinki.fi (C. Scopetani).

1. Introduction

Microplastics (MPs) pollution is an environmental issue, whose risks for human health are not yet well understood (Lee et al., 2019). What we know is that MPs are ubiquitous in marine and freshwater environments and can cause adverse health effects to the biota that mistake plastic debris for food (Andrade et al., 2019; Cincinelli et al., 2018; Dawson et al., 2018; Martellini et al., 2018; Ribeiro et al., 2018; Silva et al., 2018; Yu et al., 2018; Gewert et al., 2015; Stolte et al., 2015; Vianello et al., 2013). The vast majority of MPs studies is focused on aquatic habitats, while knowledge of microplastics pollution in terrestrial ecosystems is extremely limited. The first published research studying microplastics in soil under environmental conditions was carried out close to the industrial areas in Sydney, where Fuller and Gautam (2016) developed a method based on pressurized fluid extraction (PFE) to analyze MPs in soil samples and showed that the soil mass was composed of 0.03–6.7 w/w% MPs. In Switzerland, 90% of the studied floodplain soils were found to contain MPs with concentrations up to 55.5 mg kg⁻¹ or 593 particles kg⁻¹ (Scheurer and Bigalke, 2018).

One possible source of plastic in soils may be soil amendments like the compost made from biowaste and sewage sludge, particularly rich in organic carbon and plant nutrients (Blasing and Amelung, 2018). Wastewater treatment plants remove up to 90% of MPs from the incoming water, with the plastic debris remaining in the sludge (Mason et al., 2016; Estahbanati and Fahrenfeld, 2016; Carr et al., 2016; Mintenig et al., 2017) and reaching a concentration of 1000–24,000 plastic items kg⁻¹ (Mintenig et al., 2017; Mahon et al., 2017; Du et al., 2020). Taking into account the compost application rate, and the MPs load in the sludge, Nizzetto et al. (2016) estimated a yearly input of 63,000–430,000 and 44,000–300,000 tons of microplastics to European and North American agricultural soils, respectively. Considering all these alarming data and how little is known about MPs in terrestrial ecosystems, there is an urgent need to collect new information.

Lack of information of pollution levels is not the only gap in the scientific MPs literature. Most of the researchers agree that MPs are plastic particles smaller than 5 mm but for others the upper limit should be reduced (Hartmann et al., 2019). The definition of MPs is thus still unclear and the lack of specifications hampers progress in research (Hartmann et al., 2019). For instance, the US EPA defines MPs as plastic particles smaller than 5 mm (Environmental Protection Agency, 2011), while Hartmann et al. (2019) have suggested to define them as plastic debris in the size range of 1–1000 µm. Furthermore, there are no standardized MPs extracting methods commonly accepted within the scientific community (Silva et al., 2018; GESAMP, 2015). The discrepancy between the adopted methodologies poses serious problems regarding the comparability of different studies and the under- or overestimation of MPs concentrations (Silva et al., 2018; Scopetani et al., 2020).

The most adopted MPs extracting process from solid samples is density separation followed by filtration (Hanvey et al., 2017). This technique exploits the density difference between the polymers and the solid sample. Different brine solutions are added to the samples and after shaking and a subsequent settlement period, the supernatant is filtered with a vacuum pump and MPs are collected on a filter. The most common separation solution is composed of NaCl with a density of 1.2 g ml⁻¹ but other salts like zinc chloride (ZnCl₂), calcium chloride (CaCl₂), sodium iodide (NaI), sodium polytungstate and sodium bromide (NaBr) are also used to increase the density in order to extract higher density polymers (Hanvey et al., 2017; Liu et al., 2019). Despite this, the density separation techniques are often unable to separate the polymers with highest density (except when NaBr is used) and are usually not suitable for solid samples that contain light organic matter, such as recycled fertilizers, or for clay soils, whose fine grains remain suspended in the supernatant.

Besides density separation, a few other techniques have recently been presented in the scientific literature. Felsing et al. (2018) developed an electrostatic metal/plastic separator to physically isolate

plastics from solid samples, while Grbic et al. (2019) presented a method based on magnetic extraction, using hydrophobic Fe nanoparticles. Crichton et al. (2017) introduced an oil extraction procedure where canola oil was used to separate MPs from aquatic sediments with an average MPs recovery rate of over 96%. Mani et al. (2019) used castor oil to separate MPs from suspended surface solids (marine and fluvial), soil and sediment. They spiked the samples with polypropylene (PP), polystyrene (PS), polymethyl methacrylate (PMMA) and glycol modified polyethylene terephthalate (PET-G) polymers obtaining a mean MPs spiked-recovery rate of 99% ± 4%. However, when analyzing non-spiked fluvial suspended solid samples, the authors noticed that the majority (76%) of PS MPs were not retained in the oil layer, but instead found in the solid phase. Lares et al. (2019) tested the method presented by Crichton et al. (2017) and pointed out that ethyl alcohol was not able to remove all canola oil traces, thus hindering the identification with Raman and FTIR spectroscopy. Furthermore, Lares et al. (2019) observed that separatory funnels, technical solution adopted also by Mani et al. (2019), could easily get obstructed when extracting solid samples (e.g. compost matrix) and they restrict the upper size of recovered MPs.

All the presented methods have limitations and potential biases and there is an urgent need to develop a reliable and standardized method that could be globally adopted by the scientific community.

The aim of our research is to develop an alternative extracting technique process that could overcome the criticalities of the currently adopted methodologies. Inspired by Crichton et al. (2017) and Mani et al. (2019), we decided to modify and improve their oil extraction methods to find a methodology that would be suitable for treating compost and soil samples and that would avoid using separatory funnels, thus solving the weaknesses highlighted by Lares et al. (2019).

We performed preliminary experiments with oils of different density and polarity (e.g. rapeseed, mineral, synthetic, and olive oil) to check which had the strongest affinity with polymers and found that olive oil had the best performance. We therefore selected olive oil for the extraction of MPs from soil and compost samples.

2. Materials and methods

2.1. Test matrices and MPs

The efficiency of the method was tested for both soil and compost matrix. Soil samples were collected from two oat fields in Hollola, Finland: Simola (60° 56.650'N; 25° 29.895'E) and Mäkelä (60° 57.735'N; 25° 26.969'E). The samples were collected from the first soil layer (1–5 cm) using a metal spoon and kept in glass jars previously rinsed with ultrapure water (18.2 MΩ).

The compost samples were collected from Labio Ltd., a waste treatment company that collects and treats biowaste and sludge from wastewater treatment plants. Both composted biowaste and composted sewage sludge products were sampled using a metal shovel and kept in metal buckets previously rinsed with ultrapure water. Soil and compost samples were preserved in a cold room at 5 °C and analyzed one week after the sampling.

Six different self-made micro-polymers (range of dimension 0.2–2 mm) were used as test MPs. The polymers were assigned to one of three groups according to their density. Group 1 (low density): polyethylene (PE, 0.91–0.94 g/cm³) and polyurethane (PU, 0.05–0.07 g/cm³); Group 2 (medium density) polystyrene (PS, 1.05 g/cm³) and polycarbonate (PC, 1.20–1.22 g/cm³); Group 3 (high density): polyvinyl chloride (PVC, 1.30–1.45 g/cm³) and polyethylene terephthalate (PET, 1.39 g/cm³). These polymers were selected because they are among the most common plastic polymers produced worldwide (Plastic Europe, 2013) and their densities differ greatly. The polymers were classified into three density groups: low (density < 1 g/cm³), medium (1–1.29 g/cm³), and high (>1.3 g/cm³). Five sub-samples of each soil (each 25 g) and compost (10 g) matrices (20 sub-samples in

total) were spiked with all of the six self-made micro-polymers. Ten pieces of each polymer (60 polymer items in total) were added to each sub-sample. The pieces were analyzed with Fourier transform infrared (FTIR) spectroscopy (Bruker Alpha-P FTIR equipped with ATR) both before and after extraction.

The results on MPs recovery were not hampered by the potential MPs contained originally by the samples. The spiked MPs were self-made and clearly recognizable with the naked eye. Furthermore, the samples were carefully checked, before spiking them with MPs, to see if there was any plastic particle that could resemble the self-made ones.

The possibility of self-contamination was considered, and during all steps of the sampling, treatment and analysis of the samples, fleece clothing and other plastic items, which could release MPs, were avoided (Scopetani et al., 2020). Instead, only cotton clothes were used during sampling. Furthermore, procedural blanks were performed parallel with the samples to check for potential source of contamination coming from equipment or airborne particles and no MPs were found in any of the blanks.

2.2. Extraction method

The spiked samples were mixed with ultrapure (18.2 M Ω) water in custom-made polytetrafluoroethylene (PTFE) cylinders (25 cm length, 4 cm external diameter, 3 cm inner diameter) equipped with removable caps and a piston to push out the sample. After shaking the systems, 3 mL of oil was added. The samples were then shook again, allowing the oil to get in contact with the test matrix and the MPs. After two hours of settling, the samples were frozen at -40°C and the ice columns, together with the oil layers, were pushed out to filtering funnels. Most of ice and soil could be removed from the samples at this point. The samples were filtered through glass microfiber filters (GF/A, 90 mm diameter, Whatman). The filters were carefully rinsed with water and finally with hexane to remove oil traces, air dried, and the polymer particles were collected with tweezers and identified using FTIR. Each sample was extracted thrice in order to maximise the recovery.

We chose to use PTFE cylinders to overcome the difficulties when using separation funnels. The separation of soil and water from oil in separation funnels was found to be impractical because of the boundary layer containing both floating polymers and plant material and possible emulsion. In addition, separation funnels become easily clogged by solid material. The process of freezing the samples facilitate the separation of the oil layer from the water and the soil or compost. In this way, we were able to recover the whole oil layer without collecting any unwanted portion of the settled solid sample. The use of a freezer that reaches -40°C allows a fast freezing (2 h) and reduce the downtime optimizing the whole process.

Preliminary experiments were performed to test a larger set of polymers including polytetrafluoroethylene (PTFE) (Scopetani et al., 2019b). The obtained recovery was promising for all the polymers extracted from soil samples except for PTFE (Scopetani et al., 2019b). PTFE MPs did get up to the oil layer when the matrix was composed of oil and water only, but when soil or compost was added, the MPs stayed on the bottom. Therefore, as the method presented here is not suitable to extract PTFE MPs from solid samples, the use of PTFE tubes does not pose contamination issues.

2.3. Oxidation of the organic matter

When complex and organic-rich solid substrates like soil and compost are analyzed for MPs, it is often necessary to remove the organic content of the samples that hampers the identification of MPs. In this study, we applied a Fenton system protocol described by Qin et al. (2015), slightly modified, and checked if it could be combined with the oil extraction method. Hurley et al. (2018) identified the Fenton's

reagent as the most effective method for removing organic material without causing degradative changes to plastic particles.

Briefly, four sub-samples of Mäkelä soil and biowaste compost (8 sub-samples in total) were spiked with the same MPs (PE, PU, PC, PET, PVC, PS) used in the previous test. In addition, here we also used micro-particles from car tires, known to be one of the major sources of microplastics in the environment (Sundt et al., 2014; Essel et al., 2015; Lassen et al., 2015). Knowing that car tire rubbers are a mixture of natural rubber, styrene butadiene rubber and butadiene rubber, we wanted to see how the method works with such different material.

The spiked samples were put in glass bottles and the following reagents were added for each gram of sample: 10 mL 30% H₂O₂, 1 mL of 2 mmol/L FeSO₄·7H₂O, 1 mL of 2 mmol/L protocatechuic acid and 5 mL of H₂O (Qin et al., 2015). The bottles were first kept in the fume hood for one hour and then overnight in the oven at 40°C . We checked that the oxidation reaction did not create heat that could affect the polymers. The oxidized samples were transferred to the PTFE tubes and the oil extraction method was applied as described earlier for non-oxidized samples. The recovered polymers were analyzed using an Alpha-P FTIR-ATR spectrometer as described later in section 2.4 to check for potential changes in the polymer structures due to the oxidation process.

Loss on ignition (550°C , overnight) of compost samples showed that their average organic content was $38\% \pm 2\%$. The average mass loss of compost samples in oxidation was $36\% \pm 5\%$, which shows that the selected oxidation method was able to oxidize on average 95% of the total organic content. These results are in compliance with an earlier study, which found 80–87% removal of organics in sludge and 96–108% removal of organics in soil after applying an oxidation protocol using Fenton reagent (Hurley et al., 2018).

2.4. FTIR-ATR analysis

The PE, PU, PC, PET, PVC, PS and car tire MPs were analyzed before and after extraction using an Agilent Cary 630 FTIR Spectrometer equipped with a diamond crystal ATR (Attenuated Total Reflection) unit. Black samples (PE, rubber) were also analyzed with a germanium crystal ATR. The analyses were performed in an absorbance mode and using a resolution of 4 cm^{-1} with 32 scans for each spectrum in a spectral range from 4000 cm^{-1} to 650 cm^{-1} . The MP particles were picked by hand using forceps and placed onto the ATR crystal. The particle sizes ranged from 0.2 to 2 mm.

2.5. Microscope FTIR analysis

To further test the method and to investigate if smaller MPs originally occurred in the collected soil and compost samples, three replicates of each matrix were prepared following the procedure described above, but without spiking MPs. The dried filters were analyzed with a Cary 620–670 Fourier transform infrared spectroscopy (FTIR) microscope (Agilent Technologies) equipped with an FPA (Focal Plane Array) 128×128 detector (Agilent Technologies), which allows performing 2D imaging-FTIR analysis on MPs directly on the filters. This analytical approach for the identification of MPs has been validated in several studies by different research groups (Harrison et al., 2012; Tagg et al., 2015; Mintening et al., 2017; Andrades et al., 2018; Simon et al., 2018; Scopetani et al., 2019a.). The analyses were performed in a reflectance mode using open aperture and a spatial resolution of 4 cm^{-1} acquiring 128 scans for each spectrum. Each analysis consisted of a map of $700\text{ }\mu\text{m} \times 700\text{ }\mu\text{m}$ (128×128 pixels) and each pixel had a dimension of $5.5\text{ }\mu\text{m} \times 5.5\text{ }\mu\text{m}$ (Imaging map spatial resolution of $5.5\text{ }\mu\text{m}$). MPs were detected and identified in five randomly chosen squares ($2\text{ cm} \times 2\text{ cm}$) on each filter, comprising 31.4% of the filter area.

2.6. Statistical analysis

The main effects of polymer density group (low, medium and high density) and polymer identity (two polymers in each density group) and the interaction effects of polymer density group \times matrix class (compost and soil) and polymer density group \times oxidation on MPs extraction efficiency were tested using data of numbers of missed MPs items for each polymer in each test cylinder ($N = 168$) and a generalized linear model with negative binomial distribution and log link function. The main effects of oxidation, matrix class and matrix identity (two different compost and soil materials) and the interaction effect of matrix class \times oxidation were tested using data of total number of missed MPs items in each test cylinder ($N = 28$) and a generalized linear model with normal distribution and log link function. In the models, matrix identity was nested within matrix class and polymer identity was nested with polymer density group. Statistically significant differences among polymer density groups were tested using Bonferroni corrected pair-wise comparisons of density group means.

3. Results and discussion

3.1. Recovery of MPs

When polymers were collected and analyzed using an Alpha-P FTIR equipped with ATR, no oil traces were detected that could affect the identification. The FTIR spectra recorded before and after extraction revealed that the use of hexane and the oxidation process did not modify the FTIR spectra of MPs and no changes in the morphology or size of the MPs was observed after a visual examination.

Both the reference and the oxidized samples shared the majority of peaks (Fig. 1 and Supplementary Info) and in case of Fig. 1 they are identifiable as polystyrene. The intense absorption at 1742 cm^{-1} observed in the oxidized samples might indicate the development of carbonyl groups due to oxidation (Verleye et al., 2001).

The number of missed MPs during the extraction was affected by polymer density group ($df = 2$, Wald $\text{Chi}^2 = 12.3$, $P = 0.002$), polymer identity, which represents polymer structure ($df = 3$, Wald $\text{Chi}^2 = 10.4$,

$P = 0.015$) and matrix class, i.e. whether soil or compost was used as a test material ($df = 1$, Wald $\text{Chi}^2 = 6.85$, $P = 0.009$), whereas matrix identity, i.e. which compost or which soil was used ($df = 2$, Wald $\text{Chi}^2 = 4.15$, $P = 0.125$) and the oxidation treatment ($df = 1$, Wald $\text{Chi}^2 = 0.60$, $P = 0.439$) had no effect. Matrix class \times polymer density group interaction effect was not significant ($df = 2$, Wald $\text{Chi}^2 = 0.93$, $P = 0.628$), which indicates that differences among polymer density groups did not depend on whether they were tested in compost or soil matrix.

When the results are illustrated using MPs recovery rate (% of added items extracted), it appears that the recovery was on average lower in compost (mean recovery rate 90.5% of added items) than soil (96.5%) and on average lower for the low density polymer group (89.1%) than for the medium density (95.9%) and high density (95.5%) polymer groups (Fig. 2). Within polymer density groups, the recovery rate of polymers differed on average by 4.9% (Fig. 3).

These results suggest that the presented method has a high recovery rate of MPs. Compost materials seem to have a slightly lower recovery rate than agricultural field soils and the density and identity of polymers also play a role. Our results suggest that low density MPs are somewhat harder to extract than higher density MPs. However, this result needs to be treated cautiously as differences between polymers within polymer density groups were of similar magnitude as differences among the density groups. Significant differences within density groups suggest that other characteristics of polymers, on top of density, are also important for recovery, and therefore, the lower recovery rate of the low density group might simply arise of the characteristics of the two polymers other than density.

The mechanism of the extraction was called oleophilic interaction by Crichton et al. (2017), meaning attraction between the long chain fatty acids of the oil and the polymer back-bone. Our experiments suggest that this interaction is strong enough to bring many dense polymers to the oil layer, but not strong enough to extract fluorinated polymers, like polytetrafluoroethene from solid samples. The oil separation method can be used for the extraction of many soil types without the oxidation step. Sandy sediments, and in particular sea sand, may be an exception, however, as we have earlier shown that especially the

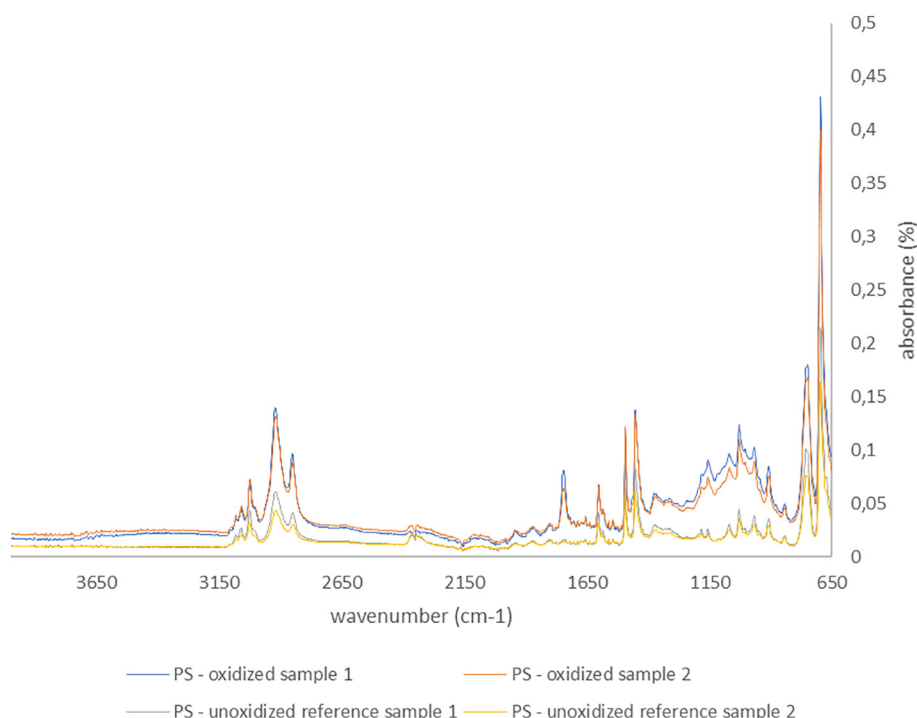


Fig. 1. FTIR spectra of two polystyrene MPs before and after the oxidation and extraction procedure.

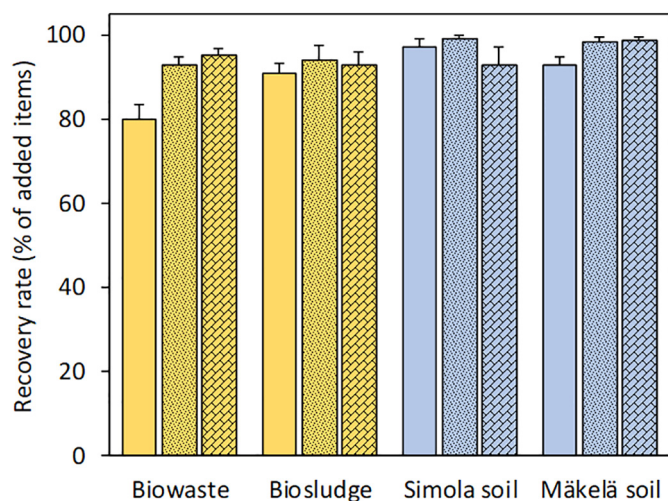


Fig. 2. MPs recovery rate (mean + SE; $n = 10-18$) for low density (plain), medium density (dotted) and high density (tiled) polymer groups in compost (yellow) and soil (blue) matrices as averaged across the oxidation treatment. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

densest polymers (e.g. poly methyl methacrylate, PC, PVC, PET) are attached to the sand (Scopetani et al., 2019b).

3.2. Recovery of car tire MPs

Car tire MPs was the only MPs type that had a low recovery rate and thus seemed to behave differently from others. The recovery rate also differed between the soil (mean recovery rate $73\% \pm 5\%$ of added items) and compost ($30\% \pm 18\%$). These results suggest that the oleophilic interaction between car tire MPs and olive oil is weaker than for the other polymers, or then the interaction between the matrix

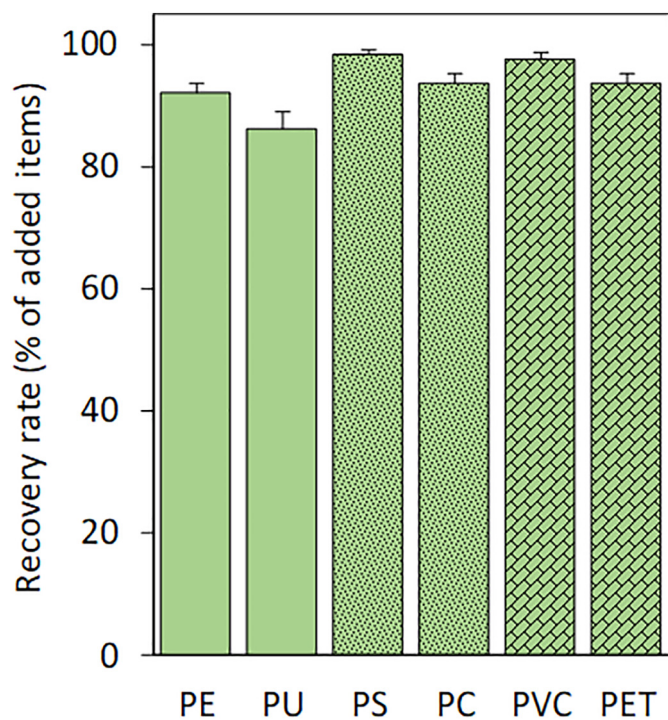


Fig. 3. MPs recovery rate (mean + SE; $n = 28$) for each polymer in low density (plain), medium density (dotted) and high density (tiled) polymer groups as averaged across all matrices and the oxidation treatment.

and tire rubber is stronger than the interaction between oil and the rubber. Further studies are clearly needed to clarify these findings.

3.3. Microscope FTIR analysis

To demonstrate the usefulness of the method for particles smaller than $300\ \mu\text{m}$, we checked the occurrence of MPs in our matrix materials using the olive oil extraction. The dried filters were analyzed using a Cary 620–670 Fourier transform infrared spectroscopy (FTIR) microscope (Agilent Technologies). In the sample collected from the Mäkelä field, two different polymers were found: one acrylonitrile (butadiene styrene) (ABS) fibre and one PS fragment. Instead, no polymers were identified in the soil collected from the Simola field. This organic field was the most isolated sampling area in this study, far away from the highway and other possible sources of MPs. Two ABS fragments and a PE fibre were detected in the sewage sludge compost, while in the biowaste compost, four polymers were recorded: one PE fragment, one PET fibre, one acrylate fragment and a blend acrylate/PET fibre. These findings show that the method also works with smaller particles (from $5\ \mu\text{m}$ to $300\ \mu\text{m}$).

The FTIR spectra of the fragment found in the Mäkelä soil (Fig. 4) present intense absorptions at $3027\ \text{cm}^{-1}$ (aromatic C–H stretching vibrations), 2908 and $2850\ \text{cm}^{-1}$ (CH_2 stretching), 1944 and $1871\ \text{cm}^{-1}$ (combination bands), $1743\ \text{cm}^{-1}$ (C=O stretching), 1601 and $1492\ \text{cm}^{-1}$ (aromatic ring stretching) and $1450\ \text{cm}^{-1}$ (CH_2 bending), which are characteristic of polystyrene (Verleye et al., 2001; Noda et al., 2007; Asensio et al., 2009; Biazar et al., 2010; Olmos et al., 2014; Jung et al., 2018).

Visible light map of a plastic fragment (A). 2D FTIR Imaging maps, where the intensity of the following bands was mapped: 3027

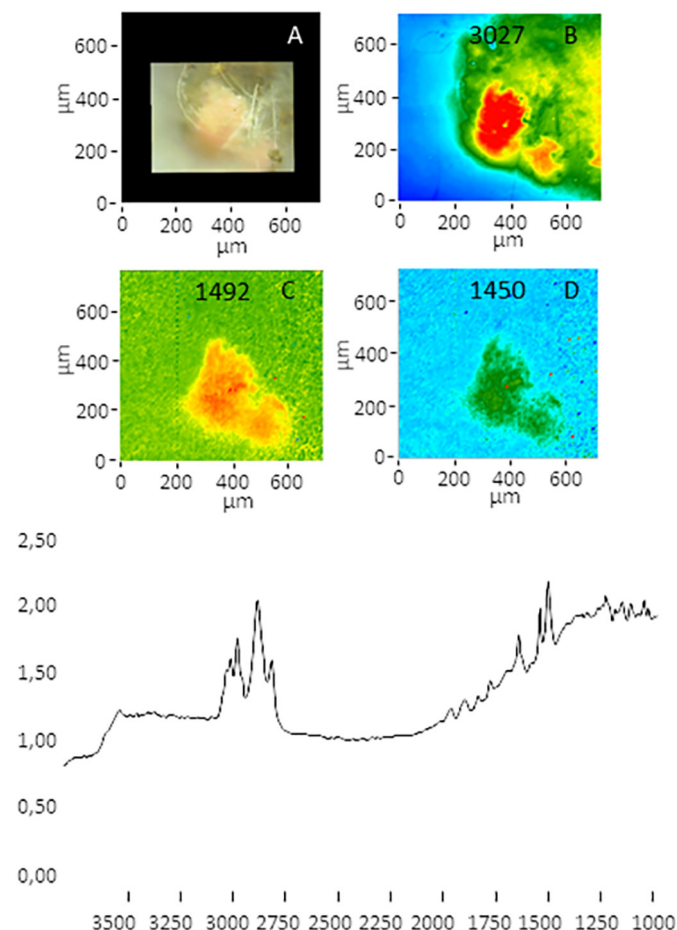


Fig. 4. FTIR spectra, visible and IR imaging of a plastic fragment found in the Mäkelä field.

(aromatic C—H stretching vibrations) (B), 1492 and 1450 cm^{-1} (carbon-carbon stretching vibrations in the aromatic ring) (C and D). The chromatic scale of each map qualitatively shows the increasing absorbance intensity as follows: blue, green, yellow, red. Maps have dimensions of $700 \times 700 \mu\text{m}^2$. The bottom panel shows the FTIR Reflectance spectrum of the plastic fragment, which relates to a single pixel ($5.5 \times 5.5 \mu\text{m}^2$) of the 2D Imaging maps.

The plastic fibre found in the same soil (Fig. 5) has intense absorptions at 2927 cm^{-1} (CH stretching), 2240 cm^{-1} (C≡N stretching), 1450 and 1369 cm^{-1} (CH₂ and CH bending), which are characteristics of polyacrylonitrile (Coates, 2000; Verleys et al., 2001), as well as bands at 1735 cm^{-1} (CO stretching) and 1246 cm^{-1} (C—O stretching), typical for acrylates (Balamurugan et al., 2004; Duan et al., 2008; Ramesh et al., 2017; Jung et al., 2018). This makes us hypothesize that the fibre is acrylonitrile-acrylate copolymer.

4. Conclusions

A clear understanding of the risks associated with MPs pollution requires reliable and accurate data on MPs occurrence in environmental samples.

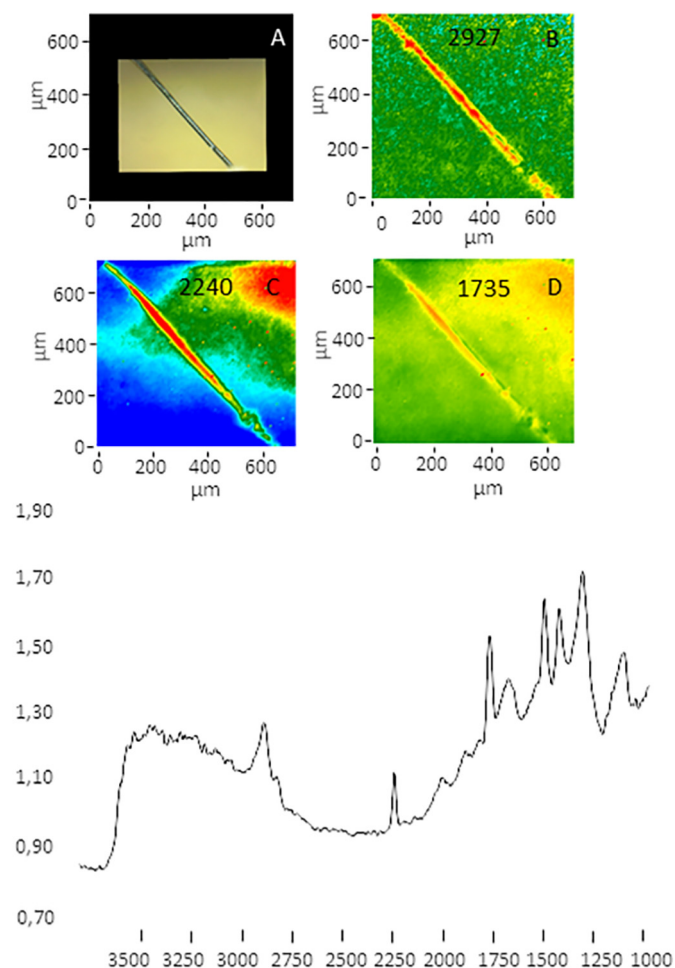


Fig. 5. FTIR spectra, visible and IR imaging of a plastic fibre found in the Mäkelä field. Visible light map of a plastic fibre (A). 2D FTIR Imaging maps, where the intensity of the following bands was mapped: 2927 (CH stretching) (B), 2240 (C—N stretching) (C), and 1735 cm^{-1} (C=O stretching) (D). The chromatic scale of each map qualitatively shows the increasing absorbance intensity as follows: blue, green, yellow, red. Maps have dimensions of $700 \times 700 \mu\text{m}^2$. The bottom panel shows the FTIR Reflectance spectra of the plastic fibre and of the neighbouring filter. Each spectrum relates to a single pixel ($5.5 \times 5.5 \mu\text{m}^2$) of the 2D Imaging maps. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

The method presented here for the extraction of MPs is easy and inexpensive and can be applied to isolate various polymers from solid samples like soil and compost.

The method was validated using six different micro-polymers: PE, PS, PVC, PC, PET and PU and low, medium and high density polymers reached a mean recovery rate of $90\% \pm 2\%$, $97\% \pm 5\%$ and $95\% \pm 4\%$, respectively. The density of the polymer seems to have only a small role in the recovery. The method is a good alternative to density separation methods as it provides as good recovery rates but no hazardous salt solutions are needed. Furthermore, density separation-based methods are often unable to extract high density polymers like PET or PVC, unlike the method presented here. The olive oil methodology can be applied to MPs of size 0.2–5 mm if a bench-top FTIR is used for the identification and down to $5 \mu\text{m}$ with a microscope-FTIR instrument.

Lares et al. (2019) showed that the weakness in the method presented by Crichton et al. (2017) is that ethyl alcohol is not able to remove all canola oil traces, thus hampering the identification with Raman and FTIR spectroscopy. Furthermore, Lares et al. (2019) pointed out that using separatory funnels, a technical solution also adopted by Mani et al. (2019), limits the upper size of recovered MPs and may not be suitable for samples that contain larger particles (e.g. compost matrix) able to obstruct the funnel. We showed that after oxidation and flushing the samples with hexane, neither oil traces nor spectral modifications were detected that could affect polymer identification. By freezing the samples, we could also avoid separation funnels and could collect the oil layer without a risk of mixing the phases.

When analyzing non-spiked fluvial suspended solid samples, Mani et al. (2019) noticed that a majority (76%) of PS MPs was not retained in the oil layer, but found in the solid phase. That we reached higher PS MPs recovery rate with our method and found PS MPs in non-spiked soil and compost samples suggest that olive oil may have better affinity for PS than the castor oil. In fact, our results suggest that olive oil may have high affinity for a wide set of polymers. Clearly though, further studies are needed to test the method with different sample matrices and to improve the efficiency in the extraction of car tire rubber and fluoropolymers.

Funding

This work was funded by Helsinki-Uusimaa Regional Council/ European Regional Development Fund within the KIEMURA – PROJECT: Circular Economy Solutions for Microplastics and Recycled Plastics. Partners: Lahti University of Applied Science, University of Helsinki, Muovipoli Oy. Additional funding was provided by Maa- ja vesitekniikan tuki ry (Land and Water Technology Foundation) within the CoTraP project.

CRediT authorship contribution statement

Costanza Scopetani: Conceptualization, Formal analysis, Investigation, Methodology, Validation, Visualization, Writing - original draft, Writing - review & editing. **David Chelazzi:** Investigation, Writing - original draft, Writing - review & editing. **Juha Mikola:** Formal analysis, Writing - original draft, Writing - review & editing. **Ville Leiniö:** Investigation, Writing - original draft. **Reijo Heikkinen:** Conceptualization, Methodology. **Alessandra Cincinelli:** Writing - original draft, Writing - review & editing. **Jukka Pellinen:** Conceptualization, Methodology, Project administration, Supervision, Validation, Writing - original draft, Writing - review & editing.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

The Consorzio Interuniversitario per lo Sviluppo dei Sistemi a Grande Interfase (CSGI), Florence, is gratefully acknowledged. Helsinki-Uusimaa Regional Council/European Regional Development Fund and Maa- ja vesitekniikan tuki ry (Land and Water Technology Foundation) are also gratefully acknowledged.

Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.scitotenv.2020.139338>.

References

- Andrade, M.C., Winemiller, K.O., Barbosa, P.S., Fortunati, A., Chelazzi, D., Cincinelli, A., et al., 2019. First account of plastic pollution impacting freshwater fishes in the Amazon: ingestion of plastic debris by piranhas and other serrasalmids with diverse feeding habits. *Environ. Pollut.* 244 776–773.
- Andrades, R., Santos, R., Joyeux, J.-C., Chelazzi, D., Cincinelli, A., Giarrizzo, T., 2018. Marine debris in Trindade island, a remote island of the south Atlantic. *Mar. Pollut. Bull.* 137, 180–184.
- Blasing, M., Amelung, W., 2018. Plastics in soil: analytical methods and possible sources. *Sci. Total Environ.* 612, 422–435.
- Carr, S., Liu, J., Tesoro, A.G., 2016. Transport and fate of microplastic particles in wastewater treatment plants. *Water Res.* 91, 174–182.
- Cincinelli, A., Scopetani, C., Guerranti, C., Chelazzi, D., Martellini, T., Giarrizzo, T., 2018. Microplastics potpourri in the Mediterranean Sea. *TrAC Trends Anal. Chem.* 110, 321–326.
- Crichton, E.M., Noël, M., Gies, E.A., Ross, P.S., 2017. A novel, density-independent and FTIR-compatible approach for the rapid extraction of microplastics from aquatic sediments. *Anal. Methods* 9 (9), 1419–1428.
- Dawson, A.L., Kawaguchi, S., King, C.K., Townsend, K.A., King, R., Huston, W.M., et al., 2018. Turning microplastics into nanoplastics through digestive fragmentation by Antarctic krill. *Nat. Commun.* 9, 1001.
- Du, C., Liang, Li, Z., Gong, J., 2020. Pollution characteristics of microplastics in soils in southeastern suburbs of Baoding City, China. *Int. J. Environ. Res. Public Health* 17, 845.
- Environmental Protection Agency, 2011. Marine Debris in North Pacific, a Summary of Existing Information and Identification of Data Gaps. US EPA-909-R-11006.
- Essel, R., Engel, L., Carus, M., Ahrens, R.H., 2015. Sources of Microplastics Relevant to Marine Protection in Germany Texte 64/2015, Report No. (UFA-FB) 002147/E. Dessau-Roßlau, Germany, Umweltbundesamt.
- Estahbanati, S., Fahrenfeld, N.L., 2016. Influence of wastewater treatment plant discharges on microplastic concentrations in surface water. *Chem* 162, 277–284.
- Felsing, S., Kochleus, C., Buchinger, S., Brennholt, N., Stock, F., Reifferscheid, G., 2018. A new approach in separating microplastics from environmental samples based on their electrostatic behaviour. *Environ. Pollut.* 234, 20–28.
- Fuller, S., Gautam, A., 2016. A procedure for measuring microplastics using pressurized fluid extraction. *Environ. Sci. Technol.* 50 (11), 5774–5780.
- GESAMP, 2015. Sources, fate and effects of microplastics in the marine environment: a global assessment. In: Kershaw, P.J. (Ed.), IMO/FAO/UNESCO-IOC/UNIDO/WMO/IAEA/UN/UNEP/UNDP Joint Group of Experts on the Scientific Aspects of Marine Environmental Protection, Rep. Stud. GESAMP No. 90, p. 96.
- Gewert, B., Plassmann, M.M., MacLeod, M., 2015. Pathways for degradation of plastic polymers floating in the marine environment. *Environ. Sci.: Processes Impacts.* 17, 1513.
- Grbic, J., Nguyen, B., Guo, E., You, J.B., Sinton, D., Rochman, C.M., 2019. Magnetic extraction of microplastics from environmental samples. *Environ Sci Technol Lett* 6 (2), 68–72.
- Hanvey, J.S., Lewis, P.J., Lavers, J.L., Crosbie, N.D., Pozo, K., Clarke, B.O., 2017. A review of analytical techniques for quantifying microplastics in sediments. *Anal. Methods* 9 (9), 1369–1383.
- Harrison, J.P., Ojeda, J.J., Romero-Gonzales, M.E., 2012. The applicability of reflectance micro-Fourier-transform infrared spectroscopy for the detection of synthetic microplastics in marine sediments. *Sci. Total Environ.* 416, 455–463.
- Hartmann, N.B., Hüffer, T., Thompson, R.C., Hassellöv, M., Verschoor, A., Daugaard, A.E., et al., 2019. Are we speaking the same language? Recommendations for a definition and categorization framework for plastic debris. *Environ. Sci. Technol.* 53, 1039–1047.
- Hurley, R.R., Lusher, A.L., Olsen, M., Nizzetto, L., 2018. Validation of a method for extracting microplastics from complex, organic-rich, environmental matrices. *Environ. Sci. Technol.* 52, 7409–7417.
- Lares, M., Ncibi, M.C., Sillanpää, M., Sillanpää, M., 2019. Intercomparison study on commonly used methods to determine microplastics in wastewater and sludge samples. *Environ. Sci. Pollut. Res.* 26 (12), 12109–12122.
- Lassen, C., Hansen, S.F., Magnusson, K., Hartmann, N.B., Rehne Jensen, P., Nielsen, T.G., et al., 2015. Microplastics: Occurrence, Effects and Sources of Releases to the Environment in Denmark. Danish Environmental Protection Agency, Copenhagen, Denmark.
- Lee, H., Kunz, A., Shim, W.J., Walther, B.A., 2019. Microplastic contamination of table salts from Taiwan, including a global review. *Sci. Rep.* 9, 1–9.
- Liu, M., Song, Y., Lu, S., Qiu, R., Hu, J., Li, X., 2019. Method for extracting soil microplastics through circulation of sodium bromide solutions. *Sci. Total Environ.* 691, 341–347.
- Mahon, A.M., O'Connell, B., Healy, M.G., O'connor, I., Officer, R., Nash, R., Morrison, L., 2017. Microplastics in sewage sludge: effects of treatment. *Environ. Sci. Technol.* 51, 810–818.
- Mani, T., Frehland, S., Kalberer, A., Burkhardt-Holm, P., 2019. Using castor oil to separate microplastics from four different environmental matrices. *Anal. Methods* 11, 1788–1794.
- Martellini, T., Guerranti, C., Scopetani, C., Ugolini, A., Chelazzi, D., Cincinelli, A., 2018. A snapshot of microplastics in the coastal areas of the Mediterranean Sea. *TrAC Trends Anal. Chem.* 109, 173–179.
- Mason, S.A., Garneau, D., Sutton, R., Chu, Y., Ehmann, K., Barnes, J., et al., 2016. Microplastic pollution is widely detected in US municipal wastewater treatment plant effluent. *Environ. Pollut.* 218, 1045–1054.
- Mintenig, S.M., Int-Veen, I., Loder, M.G.J., Primpke, S., Gerdt, G., 2017. Identification of microplastic in effluents of waste water treatment plants using focal plane array-based micro-Fourier transform infrared imaging. *Water Res.* 108, 365–372.
- Nizzetto, L., Futter, M., Langaas, S., 2016. Are agricultural soils dumps for microplastics of urban origin? *Environ. Sci. Technol.* 50, 10777–10779.
- Plastic Europe. Plastics—the facts 2013: An Analysis of European Latest Plastics Production, Demand and Waste Data. Pp 1–40 at (<http://www.mendeley.com/catalog/plasticthe-facts-2013-analysis-european-latest-plastics-production-demand-waste-data/>).
- Qin, Y., Song, F., Ai, Z., Zhang, P., Zhang, L., 2015. Protocatechuic acid promoted al-chlor degradation in Fe (III)/H₂O₂ Fenton system. *Environ Sci Technol* 49, 7948–7956.
- Ribeiro, F., O'Brien, J.W., Galloway, T., Thomas, K.V., 2018. Accumulation and fate of nano- and micro-plastics and associated contaminants in organisms. *TrAC Trends Anal. Chem.* 111, 139–147.
- Scheurer, M., Bigalke, M., 2018. Microplastics in Swiss floodplain soils. *Environ Sci Technol* 52, 3591–3598.
- Scopetani, C., Chelazzi, D., Cincinelli, A., Esterhuizen-Londt, M., 2019a. Assessment of microplastic pollution: occurrence and characterisation in Vesijärvi lake and Pikku Vesijärvi pond, Finland. *Environ. Monit. Assess.* 191, 652.
- Scopetani, C., Pflugmacher, S., Pellinen, J., 2019b. A method for the extraction of microplastics from solid samples using olive oil. Poster Session Presented at 16 Th International Conference on Environmental Science and Technology Rhodes, Greece, 4 to 7 September 2019.
- Scopetani, C., Esterhuizen-Londt, M., Chelazzi, D., Cincinelli, A., Setälä, H., Pflugmacher, S., 2020. Self-contamination from clothing in microplastics research. *Ecotoxicol. Environ. Saf.* 189, 110036.
- Silva, A.B., Bastos, A.S., Justino, C.I.L., da Costa, J.P., Duarte, A.C., Rocha-Santos, T.A.P., 2018. Microplastics in the environment: challenges in analytical chemistry—a review. *Anal. Chim. Acta* 1017, 1–19.
- Simon, M., van Alst, N., Vollertsen, J., 2018. Quantification of microplastic mass and removal rates at wastewater treatment plants applying focal plane array (FPA)-based Fourier transform infrared (FT-IR) imaging. *Water Res.* 142, 1–9.
- Stolte, A., Forster, S., Gerdt, G., Schubert, H., 2015. Microplastic concentrations in beach sediments along the German Baltic coast. *Mar. Pollut. Bull.* 99 (1–2), 216–229.
- Sundt, P., Schulze, P.-E., Syversen, F., 2014. Sources of Microplastics-Pollution to the Marine Environment. Mepex Consult AS, Asker, Norway, p. 108.
- Tagg, A.S., Sapp, M., Harrison, J.P., Ojeda, J.J., 2015. Identification and quantification of microplastics in wastewater using focal plane array-based reflectance micro-FT-IR imaging. *Anal. Chem.* 87 (12), 6032–6040.
- Vianello, A., Boldrin, A., Guerriero, P., Moschino, V., Rella, R., Sturaro, A., et al., 2013. Microplastic particles in sediments of lagoon of Venice, Italy: first observations on occurrence, spatial patterns and identification. *Estuar. Coast. Shelf Sci.* 130, 54–61.
- Yu, Y., Zhou, D., Li, Z., Zhu, C., 2018. Advancement and challenges of microplastic pollution in the aquatic environment: a review. *Water Air Soil Pollut.* 229, 140.