



UNIVERSITÀ
DEGLI STUDI
FIRENZE

FLORE

Repository istituzionale dell'Università degli Studi di Firenze

Sonocrystallization as an Efficient Way to Control the Size, Morphology, and Purity of Coordination Compound Microcrystallites:

Questa è la Versione finale referata (Post print/Accepted manuscript) della seguente pubblicazione:

Original Citation:

Sonocrystallization as an Efficient Way to Control the Size, Morphology, and Purity of Coordination Compound Microcrystallites: Application to a Single-Chain Magnet / Evrard Q.; Houard F.; Daiguebonne C.; Calvez G.; Suffren Y.; Guillou O.; Mannini M.; Bernot K.. - In: INORGANIC CHEMISTRY. - ISSN 0020-1669. - STAMPA. - 59:(2020), pp. 9215-9226. [10.1021/acs.inorgchem.0c01126]

Availability:

The webpage <https://hdl.handle.net/2158/1237780> of the repository was last updated on 2022-02-17T17:00:34Z

Published version:

DOI: 10.1021/acs.inorgchem.0c01126

Terms of use:

Open Access

La pubblicazione è resa disponibile sotto le norme e i termini della licenza di deposito, secondo quanto stabilito dalla Policy per l'accesso aperto dell'Università degli Studi di Firenze (<https://www.sba.unifi.it/upload/policy-oa-2016-1.pdf>)

Publisher copyright claim:

Conformità alle politiche dell'editore / Compliance to publisher's policies

Questa versione della pubblicazione è conforme a quanto richiesto dalle politiche dell'editore in materia di copyright.

This version of the publication conforms to the publisher's copyright policies.

La data sopra indicata si riferisce all'ultimo aggiornamento della scheda del Repository FloRe - The above-mentioned date refers to the last update of the record in the Institutional Repository FloRe

(Article begins on next page)



Space charge-limited current transport mechanism in crossbar junction embedding molecular spin crossovers

Giuseppe Cucinotta, Lorenzo Poggini, Niccolò Giaconi, Alberto Cini, Mathieu Gonidec, Matteo Atzori, Enrico Berretti, Alessandro Lavacchi, Maria Fittipaldi, Aleksandr I. Chumakov, et al.

► To cite this version:

Giuseppe Cucinotta, Lorenzo Poggini, Niccolò Giaconi, Alberto Cini, Mathieu Gonidec, et al.. Space charge-limited current transport mechanism in crossbar junction embedding molecular spin crossovers. ACS Applied Materials & Interfaces, Washington, D.C. : American Chemical Society, 2020, 12 (28), pp.31696-31705. 10.1021/acsami.0c07445 . hal-02906236

HAL Id: hal-02906236

<https://hal.archives-ouvertes.fr/hal-02906236>

Submitted on 17 Sep 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Space charge limited current transport mechanism in crossbar junction embedding molecular spin crossovers

Giuseppe Cucinotta,^{1,‡,} Lorenzo Poggini,^{1,2,‡,*} Niccolò Giaconi,¹ Alberto Cini,³ Mathieu
Gonidec,² Matteo Atzori,^{1,†} Enrico Berretti,⁴ Alessandro Lavacchi,⁴ Maria Fittipaldi,³ Aleksandr
I. Chumakov,⁵ Rudolf Rüffer,⁵ Patrick Rosa,² Matteo Mannini.¹*

1) Department of Chemistry “U. Schiff” and INSTM Research Unit, University of Florence, Via
della Lastruccia 3-13, 50019 Sesto Fiorentino (FI), Italy

2) CNRS, University of Bordeaux, ICMCB, UMR 5026, 33600 Pessac, France

3) Department of Physics and Astronomy and INSTM Research Unit, University of Florence, Via
Sansone 1, 50019 Sesto Fiorentino (FI), Italy

4) Institute for Chemistry of OrganoMetallic Compounds (ICCOM-CNR), Via Madonna del
Piano, 50019 Sesto Fiorentino (FI), Italy

5) ESRF-The European Synchrotron, Avenue des Martyrs 71, 38000 Grenoble, France

KEYWORDS

Spin crossover, transport measurements, hybrid device, FIB-STEM, synchrotron Mössbauer spectroscopy, molecular magnetism, molecular spintronics

ABSTRACT

Spin crossover complexes are among the most studied classes of molecular switches and have attracted considerable attention for their potential technological use as active units in multifunctional devices. A fundamental step towards their practical implementation is the integration in macroscopic devices adopting hybrid vertical architectures. Firstly, the physical properties of technological interest shown by these materials in the bulk phase have to be retained once they are deposited on a solid surface. Herein, we describe the study of a hybrid molecular inorganic junction embedding the spin crossover complex $[\text{Fe}(\text{qnal})_2]$ (qnal = quinoline-naphtaldehyde) as an active switchable thin film sandwiched within energy optimized metallic electrodes. In these junctions, developed and characterized with the support of state of the art techniques including synchrotron Mössbauer source (SMS) spectroscopy and focused-ion beam scanning transmission electron microscopy, we observed that the spin state conversion of the Fe(II)-based spin crossover film is associated with a transition from a space charge limited current (SCLC) transport mechanism with shallow traps to a SCLC mechanism characterized by the presence of an exponential distribution of traps in concomitance with the spin transition temperature.

INTRODUCTION

Nowadays molecule-based materials represent a good alternative to conventional inorganic semiconductor materials for the development of innovative devices as a consequence of their rich tunability of the molecular properties.¹⁻³ Moreover, the processability and the light weight of organic materials permit the production of flexible devices,^{4,5} a key aspect for next generation devices. Spin crossover (SCO) complexes, are molecular compounds able to reversibly switch their physical properties upon application of external stimuli (temperature, light-irradiation, applied magnetic and electric fields, pressure, *etc.*). This is associated to a switch of the spin state between two magnetic states (low-spin, LS, and high-spin, HS) of a coordinated metal ion. These inorganic complexes have been proposed as active materials in functional devices with reversible magnetic and electrical response.⁶⁻¹⁴ To the best of our knowledge, only a few reported studies deal with the integration of SCO materials in electrical and electromechanical devices,^{6,15} since the preparation of high-quality thin films and electronically optimized hybrid architectures is critical. Most studies have been focused on rather thick films of highly insulating compounds that may operate in the hopping regime in order to limit problems associated to the device preparation, such as percolation and short-circuits issues.¹⁰ However, entering in the domain of spintronics, interfacial phenomena play a crucial role. In this context, it is important to increase the general knowledge on devices based on thinner molecular layers.¹⁶ Some of us have previously studied^{12,13} the transport properties of vertical junctions incorporating very thin films of SCO complexes formulated as $[\text{Fe}(\text{HB}(\text{trz})_3)_2]$ ($\text{HB}(\text{trz})_3$ = tris(1*H*-1,2,4-triazol-1-yl)borohydride) and $[\text{Fe}(\text{H}_2\text{B}(\text{pz})_2)_2(\text{phen})]$ ($\text{H}_2\text{B}(\text{pz})_2$ = bis(pyrazol-1-yl)borohydride, phen = 1,10-phenanthroline), demonstrating that different transport mechanisms can occur. This has been done by the use of a vertical junction architecture,^{12,13} based on a soft eutectic GaIn liquid top electrode (EGaIn)¹⁷

allowing a gentle contact with ultra-thin films. In this context, we have also recently shown that the ferrous complex $[\text{Fe}(\text{qnal})_2]$ (Hqnal = quinoline-naphtaldehyde) is an ideal target toward the integration of molecular spin crossover in vertical devices, since it can be deposited as very smooth high-quality ultra-thin films by thermal sublimation while maintaining its bulk properties with a slight shift in the spin crossover temperature $T_{1/2}$ (ca. 10 K) observed at ca. 220 K.¹⁸

In this paper, we report the development of an $\text{Ag}/[\text{Fe}(\text{qnal})_2]/\text{LiF}/\text{Au}$ multilayer device to study the mechanism which determine the current flowing across these junctions as a function of the temperature, with the support of gas-phase DFT calculations, electrochemistry, magnetization measurements, synchrotron Mössbauer source (SMS) spectroscopy and focused ion beam scanning transmission electron microscopy (FIB-STEM). LiF was used as an intercalation layer between the molecular film and the top electrode to prevent unwanted short-circuits across the molecular layer and to modulate the work function of the metallic electrodes.^{19,20} We show that in this device, there is a change in the temperature dependence of current density at the temperature at which the switching between HS and LS states occurs. More precisely, we show that the system is in a low conductance state, with no evident temperature dependence when the compound is in the LS state. When it switches to the HS state, the device then switches to a high conductance state characterized by the presence of thermal activation mechanisms at higher temperature. In addition, the analysis of the current density dependence on applied voltage reveals that the electric transport is described by a transition from space charge limited current (SCLC) with shallow traps²¹ at low temperature to SCLC with an exponential trap distribution²¹ at high temperature.

RESULTS AND DISCUSSION

[Fe(qnal)₂] were synthesized following the literature procedures^{22,23} and the details are reported in Supporting Information and in Methods part (see Synthesis Section, Figure S1 and S2). [Fe(qnal)₂] shows a molecular structure in which a hexacoordinated Fe(II) ion features a slightly distorted octahedral coordination geometry (insert in Figure 1). Thanks to four Nitrogen atoms and two Oxygen donor atoms, the qnal ligand field provides an appropriate strength to stabilize the diamagnetic LS state at low temperature (below 150 K), and the paramagnetic HS state at high temperature (above 250 K).^{18,24} The low temperature phase is characterized by an Fe^{II} ion featuring an octahedral coordination geometry which is only slightly distorted by the coordination with the ligand, with average M–N(O) distances of ca. 1.94 Å, while in the high temperature phase, the coordination octahedron is highly distorted and associated to longer M–N(O) distances, on average ca. 2.11 Å. This is associated to the partial promotion of *d*-electrons located in bonding/nonbonding orbitals (*t*_{2g}) to those having an antibonding character (*e*_g) when passing from the low to the high temperature phase.²⁵ Consequently, the total volume of the unit cell reversibly changes from 1568 Å³ (low temperature) to 1619 Å³ (high temperature) without loss of crystallinity. Bulk magnetic measurements of [Fe(qnal)₂] (see Figure 1) show an abrupt SCO behavior with a *T*_{1/2} (225 ± 1 K)¹⁸ close to that reported in the seminal work of Kuroda-Sowa and coworkers (218 K).²³ Magnetic measurements on a microcrystalline powder of the same complex isotopically enriched in ⁵⁷Fe, [⁵⁷Fe(qnal)₂] relies as well in an abrupt transition at 225 ± 1 K (see Figure S2). This thermal behavior has been confirmed by the analysis of standard transmission Mössbauer spectra of bulk [⁵⁷Fe(qnal)₂], as reported in Figure 1 (green dots), pointing out a *T*_{1/2} = 225 ± 4 K. The complete series of the Mössbauer spectra as a function of temperature is reported in Figure S3.

Earlier reports evidenced that $[\text{Fe}(\text{qnal})_2]$ exhibits the possibility to induce the SCO through light-irradiation (Light-Induced Excited Spin State Trapping, LIESST) at cryogenic temperature ($\lambda = 531 \text{ nm}$) in bulk²³ as well as once it is deposited as a thin film.¹⁸ It was also shown that after a thermal treatment at ca. 460 K at ambient pressure and under high vacuum condition, a release of the crystallization CH_2Cl_2 molecule leads to the formation of the unsolvated form $[\text{Fe}(\text{qnal})_2]$, which is accompanied with a modification of the $T_{1/2}$.^{18,23}

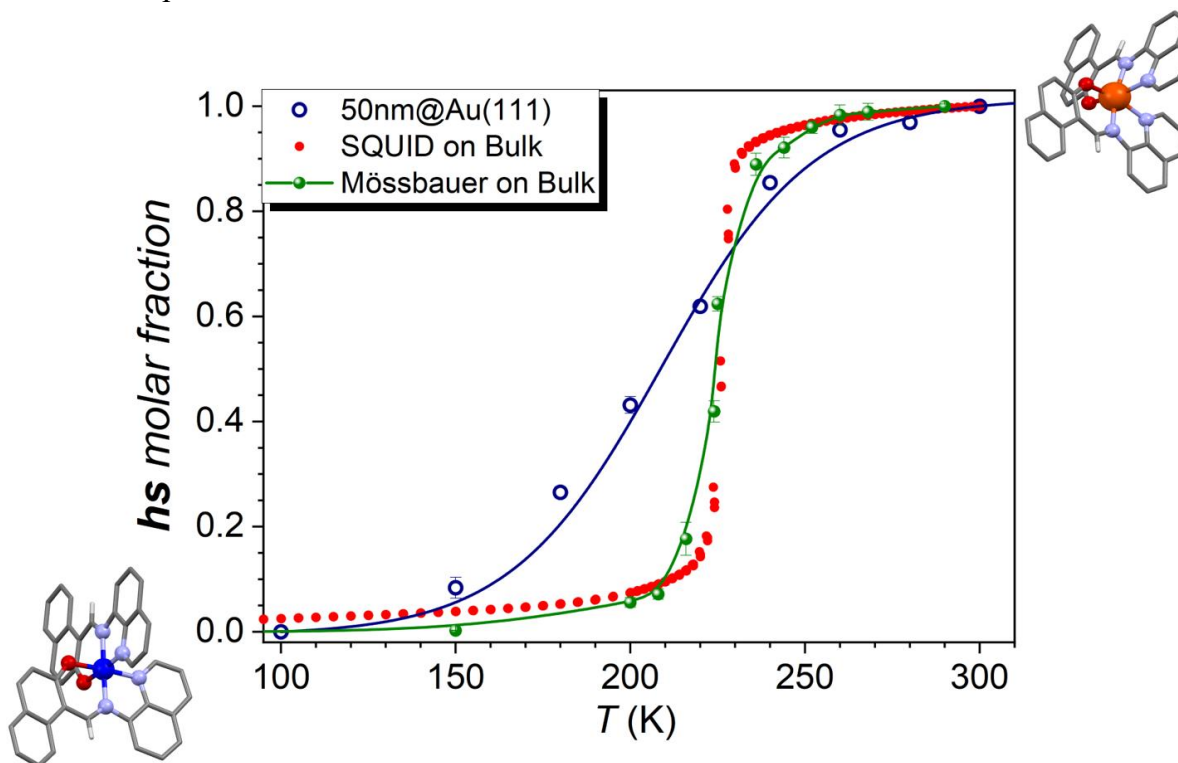


Figure 1. Comparison between bulk SQUID magnetic characterization (red dots), Mössbauer spectroscopy of $[\text{Fe}(\text{qnal})_2]$ in bulk (green dots, the line is a guide for the eyes) and High-Spin Fe(II) thermal distribution profile obtained from XAS on a thin film (blue dots). The blue line is the best fit to a Boltzmann distribution of the XAS data giving a $T_{1/2} = 210 \pm 5 \text{ K}$ (originally reported in reference 18); the total electron yield mode used in ref 18 to characterize the LS-HS conversion is surface sensitive thus providing information only on the topmost molecular layers and cannot be considered informative as the SMS spectroscopy respective to the entire deposit.

SMS spectroscopy study was performed initially on a thick film obtained by dropcasting a concentrated solution of $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ in CH_2Cl_2 and subsequently on a sublimated film. SMS spectra of the $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ dropcast sample, whose average thickness, evaluated with the SMS fitting, was 360 ± 20 nm, are reported in Figure 2a, evidencing that a complete spin conversion is encountered, as in the bulk (Figure S3). At 290 K, a HS state characterized by an isomer shift $\delta = 0.890 \pm 0.003$ mm/s and a quadrupole splitting $\Delta E_Q = 2.496 \pm 0.006$ mm/s is present, while at 3.0 K a LS state with $\delta = 0.381 \pm 0.001$ mm/s and $\Delta E_Q = 1.198 \pm 0.001$ mm/s is found. The hyperfine

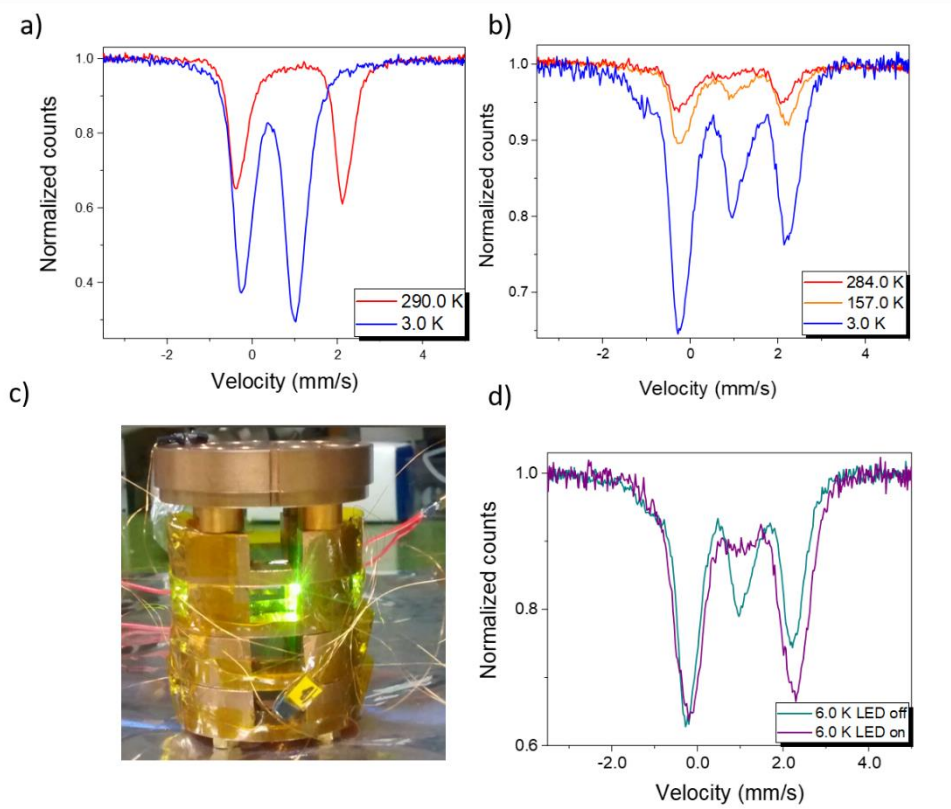


Figure 2. **a)** Synchrotron Mössbauer source spectra of the dropcast sample of $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ at 3.0 K (blue line) and at 290 K (red line) **b)** Synchrotron Mössbauer source spectra of the 100 nm thick sublimated sample of $^{57}[\text{Fe}(\text{qnal})_2]$ at different temperatures. The complete temperature trend is reported in Figure S4. **c)** Image of the sample holder with LEDs mounted to obtain the LIESST measurements. **d)** Synchrotron Mössbauer source spectra of the 100 nm thick sublimated sample of $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ acquired at 6.0 K before and after irradiation with $\lambda = 531$ nm.

values of the HS and LS states are comparable with those found using standard Mössbauer Spectroscopy for $[^{57}\text{Fe}(\text{qnal})_2]$ in the bulk phase (see Table S1).

Moving to the sublimated 100 nm thick film (Figure 2b), it can be noticed that at 3.0 K there is still a high contribution of HS, exemplified by the persistence in the spectrum of a third line above 2 mm/s. Similar hyperfine values are found for the HS and LS states, although characterized by different Gaussian distributions (see Table S1). Moreover, as one can notice from the fitting of the temperature trend (see Figure S4) the SCO efficiency is of the order of 20 %. A reduction of the SCO efficiency when molecules are deposited on a substrate is not unexpected and can be associated to the interaction with the substrate as well as to a different organization of the sublimated molecules with respect to the bulk phase.^{26–31} A similar efficiency is encountered after LIESST with $\lambda = 531$ nm (for 10 minutes with a total power 4 mW, Figures 2c-d) where after the light irradiation at 6.0 K the system reaches a HS fraction of 90 ± 6 % (starting from an HS fraction of 70 ± 4 % before irradiation) suggesting that the same fraction of molecules that can be converted with temperature can be also switched optically at low temperature. We have previously observed a similar behavior on another SCO compound on the same substrate.³²

In order to have a complete picture of the expected functionality of $[\text{Fe}(\text{qnal})_2]$ in a device, and before assembling a vertical architecture embedding it, we performed gas-phase DFT calculations (see Methods for details) for $[\text{Fe}(\text{qnal})_2]$ in both spin states and estimated the HOMO and LUMO orbital energies using Koopman's theorem.³³ As mentioned earlier, charge transport through thin dielectric films, in general, can occur via a variety of mechanisms. It follows, as we have shown recently, that varying the nature of the SCO compounds in vertical devices can lead to significant changes in the temperature dependent characteristics, as some compounds present clear tunnel-like behaviors while others exhibit thermally activated transport. In order to properly describe the

occurring processes, it is important to get reasonable estimates of the energy of the molecular orbitals involved in charge transport (in both HS and LS states). Our DFT analysis as expected for Fe(II) complexes,³⁴ evidences that the HOMO orbitals of both states (-4.66 and -4.49 eV, for the LS and the HS states, respectively) are much closer in energy to the tabulated work functions of the Ag (-4.26 eV) and LiFAu (-4.37 eV) electrodes^{19,35} (see Figure 3a) than the respective LUMO orbitals (-3.24 and -3.19 eV, respectively). This points out that charge transport in [Fe(qnal)₂] is likely to be dominated by hole transport. It is noteworthy that the estimated HOMO energies for [Fe(qnal)₂]_{LS} and [Fe(qnal)₂]_{HS}, are quite high values when compared with other Fe(II) compounds,^{12,13} and suggest that [Fe(qnal)₂] could better act as a conducting layer than other systems previously used to assemble hybrid devices.^{12,13} To ascertain the accuracy of energy estimations, we performed in parallel room-temperature solution electrochemistry experiments (see Figure S5) to get an independent estimation of the HOMO orbital energy of the HS state (that should be populated almost quantitatively at room temperature). The Fe(II)/Fe(III) redox couple was therefore measured to be $E_{1/2} = -0.62$ vs. Fc/Fc⁺ in dichloromethane containing 0.1M *n*Bu₄PF₆ as supporting electrolyte. Assuming that $E_{\text{HOMO}} \approx E_{\text{NHE}} + E_{1/2\text{vs.NHE}}$, we extracted a value of -4.52 eV for the HOMO of [Fe(qnal)₂]_{HS} which is in excellent agreement with the values calculated by DFT.

As bottom electrodes for the vertical device, we used Ag template-stripped patterned layers which provide high-quality metal-films with a very low roughness.³⁶ This was crucial to limit short-circuits problems that are also often associated to the roughness of the metal films and the inhomogeneities in the molecular film. However, in this case, the latter has been excluded because of the high-quality ultra-thin films of [Fe(qnal)₂], as estimated by the AFM analysis (Figure S6) of the deposited material. This analysis evidenced a nice defect-free SCO deposit excluding the

presence of pin-holes on the surface and Vollmer–Weber growth (figure S6c) and an RMS roughness of about. 1.1 ± 0.1 nm over an area of $23 \mu\text{m}^2$. The thickness of the “active” layer of $[\text{Fe}(\text{qnal})_2]$ deposited on top of the Ag electrodes was about 50 nm (effective thickness equal to 47 nm estimated by an AFM test, see Methods). The stacked devices were completed, as described in the Methods section and reported in Figure S7, with the deposition of a ca. 35 nm thick Au crossbar. To avoid gold percolation through the molecular film that could lead to short-circuits in the final device, a 10nm LiF intercalation layer was evaporated before gold deposition.

One of the devices used for the transport measurements (see below) was *a posteriori* characterized morphologically by STEM imaging on a lamella, extracted from a device surface using Focused Ion Beam methods. The nature of this procedure enabled the stratigraphic study of this ultra-thin stacks of heterogeneous materials, allowing the precise thickness determination of the single layers and excluding significative interdiffusion among them. In Figure 3b a STEM Dark Field image of the device section is reported. Layer thicknesses have been determined as described in Methods.

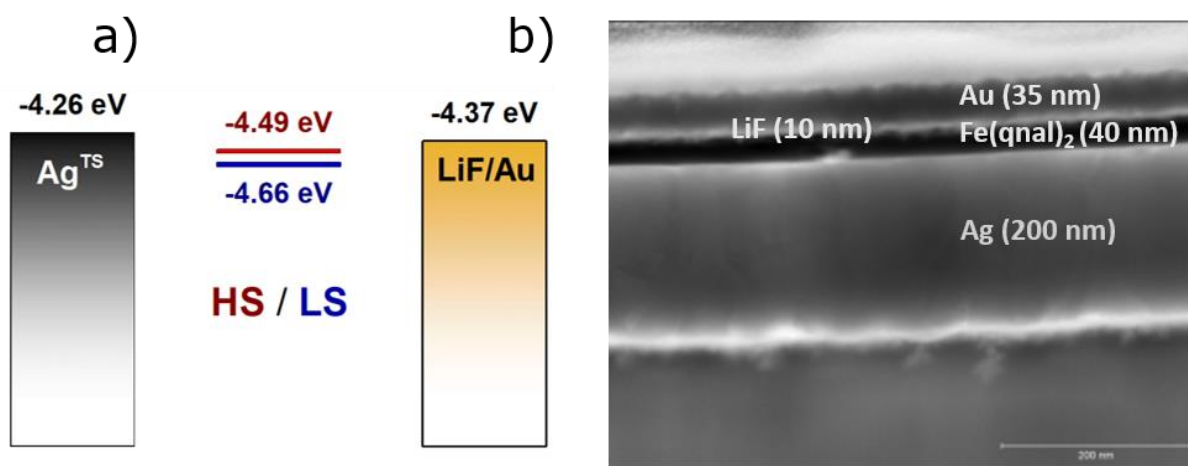


Figure 3. **a)** Electronic configuration of the junctions in open circuit for the Ag and LiF/Au electrodes and for both HS (red line) and LS (blue line) states; **b)** Dark field STEM image of a thin section of a device with different layers and thicknesses indicated.

Electric transport properties of the hybrid devices have been studied connecting the Ag and Au stripes and measuring the current flowing as a function of applied voltages by varying the temperature between 135 and 310 K. Considering the rather good energy alignment between reference values for the work functions of Ag and LiF/Au,^{19,35} and the estimated HOMO orbital energies for both [Fe(qnal)₂]_{HS} and [Fe(qnal)₂]_{LS} (see Figure 3a), the collected data have been analyzed according to SCLC model.³⁷ SCLC usually occurs when charges are injected from a metallic electrode to a dielectric such as an insulator or a wide-gap semiconductor: at the interface a space charge region arises which controls the current through the medium. For low voltages and low charge injection, electric current is mainly due to free charges present in the dielectric and follows an ohmic behaviour²¹:

$$J = \sigma_{\Omega} \frac{V}{d} = en_0\mu \frac{V}{d} \quad (1)$$

being e the electric charge, n_0 the free electron density, μ the electron mobility and d the thickness of the dielectric. When the density of injected charges starts becoming comparable to n_0 , SCLC injection takes place and, for ideal dielectrics, the current density is described³⁸ by $J \propto V^2/d^3$. Actually, real dielectrics are characterized by the presence of lattice defects, impurities, etc. that can give rise to the presence of electron traps, *i.e.* states inside the energy gap that can capture electrons by removing them from the conduction band and so reducing the current flow. Taking into account also the presence of electron traps, the relation linking J on voltage depends on the energy distribution of traps.²¹ In particular we consider the cases of shallow traps and of exponentially distributed traps. In the former, the energy of the traps is close to the edge of the conduction band ($E_c - E_t \ll k_B T$) and J is given by:

$$J = \sigma_{ST} \frac{V^2}{d^3} = \frac{9}{8} \mu \epsilon \vartheta \frac{V^2}{d^3} , \quad \vartheta = \frac{N_c}{N_t} \exp\left(-\frac{E_c - E_t}{k_B T}\right) \quad (2)$$

with ϑ representing the fraction of free electrons obtained as the ratio between the number of states at the bottom of conduction band, N_c , and the number of trap states, N_t .

If the traps present an exponential energy distribution $N_t(E) = N_{t0} \exp\left(-\frac{E_c - E}{k_B T_t}\right)$ the current density is described by the equation:³⁷

$$J = \sigma_E \frac{V^{l+1}}{d^{2l+1}} = e \mu N_c \left(\frac{\epsilon}{e N_{t0} T_t}\right)^l \frac{V^{l+1}}{d^{2l+1}} , \quad l = \frac{T_t}{T} > 1 \quad (3)$$

where the *trap distribution temperature* T_t is a parameter related to the energy width of the exponential trap distribution $k_B T_t$.

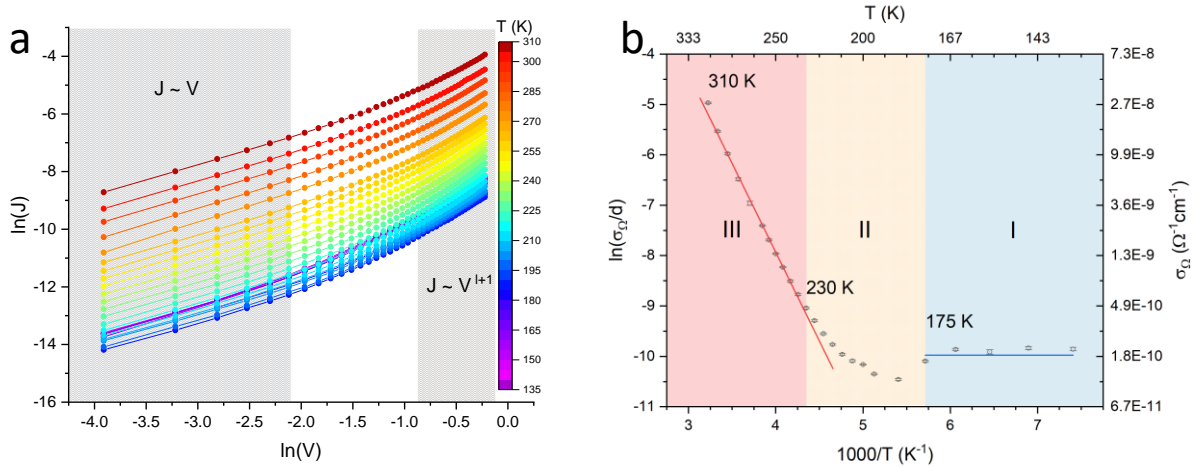


Figure 4 **a)** log-log plots of J - V characteristics at different temperatures (temperature colour-scaled as per the legend) for one of the realized devices. Low voltage ohmic and high voltage SCLC regimes voltage ranges are highlighted. **b)** logarithm of conductivities measured in the ohmic regime as function of $1/T$ revealing three temperature ranges characterized by different temperature dependence: at low temperatures (I) no presence of thermal activation processes are observed, while an Arrhenius activation mechanism is observed at higher temperatures (III).

The J - V curves collected at different temperatures in the range 135 – 310 K for one of the devices realized are reported in Figure 4a. All the J - V characteristics, as expected in presence of SCLC, show an ohmic behavior $J \sim V$ at low voltages and a super-linear dependence $J \sim V^\alpha$ ($\alpha \geq 2$) at high voltages. Linear fits of $\ln(J)$ - $\ln(V)$ curves in the ohmic region, constraining slope to 1 (see Figure S8), allowed to obtain from the intercept the values of σ_Ω that, once reported as a function of $1/T$ (see Figure 4b), revealed the presence of two distinct regimes characterized by a different dependence of σ_Ω on temperature (labelled I and III in Figure 4b) separated by a transition region (II). In the first range (I, $T \leq 175$ K) no temperature dependence is present, indicating that the measured current is due to free-charges present in the material with no contribution of thermally generated free charges. On the contrary, an Arrhenius type activation mechanism is observed in range III ($T \geq 230$ K) the fit of which provides an activation barrier of $\phi = (304 \pm 3)$ meV. Referring to Equation (1), the temperature trend of σ_Ω was ascribed to n_0 , $\sigma(T) \propto n_0(T) = \bar{n}_0 \exp\left(-\frac{\phi}{k_B T}\right)$, and ϕ was consequently considered as the activation barrier for thermally generated free-charges. Furthermore, given the good agreement between the temperature ranges I, II, III characterizing the $\sigma_\Omega(T)$ behavior with the LS–HS temperature dependence of $[\text{Fe}(\text{qnal})_2]$ (see Figure 1), we link the transport properties observed in interval I and III to the LS and HS states of $[\text{Fe}(\text{qnal})_2]$ respectively. The results coming from the analysis of the currents measured at higher voltages revealed also different trends occurring in the temperature intervals I, II and III. For temperatures lower than 175 K the current showed a quadratic dependence on voltage (see Figure S9) in accordance with a presence of shallow traps (Equation 2) while in the temperature ranges II and III a more than quadratic dependence is observed, which is consistent with the presence of an exponential trap distribution. In particular, from Equation 3 it follows that $\ln(J) = \ln\left(\frac{\sigma_E}{d^{2l+1}}\right) + (l+1) \ln(V)$ so the slope of a linear fit in a log-log plot (see Figure S10) allowed

the determination of the width of the exponential distribution $k_B T_t$. The presence of two different energy distributions of traps (shallow and exponential) can be explained as due to the different packing of the LS and HS states for $[\text{Fe}(\text{qnal})_2]$, and the ensuing different overlap between the aromatic moieties of the ligand in the molecules which are probably crucially associated to the transport mechanism.^{23,30} In Figure 5 are reported the values of the trap distribution temperature T_t obtained from the analysis of J - V characteristics in II and III as a function of temperature. For temperature range I, since no trap distribution is involved in transport mechanism, no temperature trap distribution is defined (see Equation 2) so a fictitious values $T_t = T$ was considered imposing to Equation 3 a quadratic voltage dependence to resemble that of Equation 2. The data confirm a transition, occurring in the temperature range II, from a SCLC mechanism with shallow traps in I

($T_t = T$) to one with an exponential trap distribution in III (T_t constant). A Boltzmann sigmoidal function $T_t(T) = T_{tHS} + \frac{T_{tLS} - T_{tHS}}{1 + \exp\left(\frac{T - T_{1/2}}{\Delta T}\right)}$ was used to analyze the data, being $T_{tLS} = T$ and T_{tHS} the values of T_t in the equilibrium LS and HS states respectively while ΔT is related to the slope of the transition. Results of the fit led to $\Delta T = (8.1 \pm 1.1)$ K, $T_{1/2} = (196.5 \pm 1.2)$ K, and $T_{tHS} = (354 \pm 3)$ K corresponding to a trap distribution width of $k_B T_{tHS} = (30.4 \pm 3)$ meV. In particular, the $T_{1/2}$ value obtained is consistent with the results obtained with SMS spectroscopy showing a decrease of SCO efficiency once the molecules are deposited as film. Indeed, the $T_{1/2}$ value obtained from transport measurements is lower than the ones evidenced by magnetic and Mössbauer measurements on the bulk. Moreover comparison with the $T_{1/2}$ value obtained with XAS

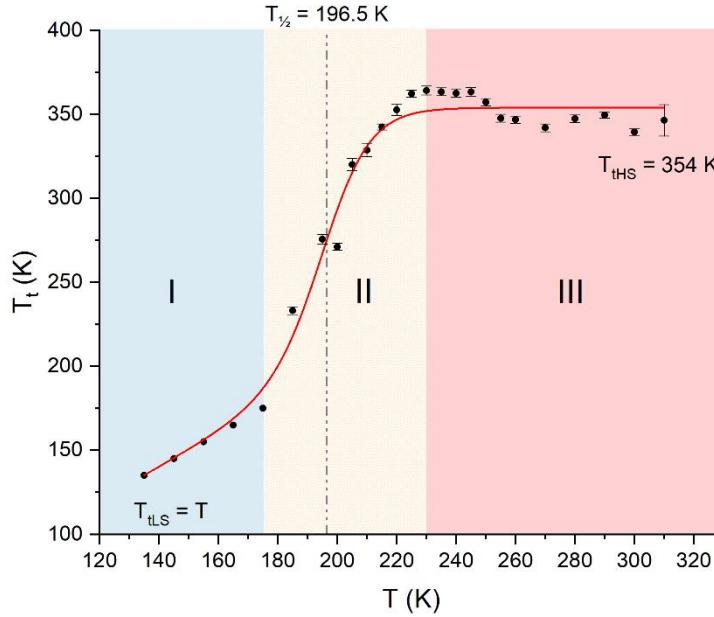


Figure 5 Trend of the T_t parameter obtained from J - V analysis (black dots) as function of temperatures. A transition between shallow traps SCLC (I, $T_t = T$) to exponential traps distribution SCLC (III) consistent with the LS – HS transition is observed. The result of the fit with a Boltzmann sigmoidal function is shown (red line) together with the related $T_{1/2}$.

measurements on a film¹⁸ suggests that the origin of the decrease of SCO efficiency can be addressed to molecular layers closer to the electrode. Indeed, XAS techniques allows the characterization of the topmost ~ 10 nm, far from the electrode/SCO interface. Moreover it provides a $T_{1/2} = 210$ K much closer to the bulk value of 225 K as compared to the value $T_{1/2} = 196.5$ K obtained from measurements of transport properties which are determined over the whole $[\text{Fe}(\text{qnal})_2]$ film.

CONCLUSIONS

A hybrid device embedding, in a vertical architecture, an Fe^{II} based molecular thin layer has been developed and state of the art synchrotron-based Mössbauer characterization of the molecular spin-crossover layer and FIB-STEM characterization of the stacked layer have been performed preliminarily to the device functional properties tests. The study of the J - V characteristics of the device as a function of the temperature, corroborated by a DFT modelling of the hybrid molecular inorganic junction, revealed the occurrence of a SCLC transport mechanism. A deeper analysis also highlights a transition from a phase characterized by shallow traps in correspondence to the LS state to a phase where an exponential traps distribution determines the transport properties in the temperature range where $[\text{Fe}(\text{qnal})_2]$ is in the HS state. In particular, we obtained evidence that the thin molecular layer of $[\text{Fe}(\text{qnal})_2]$ embedded in the vertical structure presents a fraction of molecules still retaining a SCO behavior and capable of affecting the electronic transport properties of the device. These results confirm the potential of SCO molecules and particularly $[\text{Fe}(\text{qnal})_2]$ as suitable molecules for technological applications where the occurring SCO transition triggers a change in the electronic behavior of the device. We also expect that hybrid devices with sharper and stronger responses can be obtained in the future by increasing the fraction

of molecules capable of maintaining SCO behavior once deposited on surfaces, a target which probably requires a fine tuning of the structure of the molecules, a high order of the films, and playing on ad hoc developed decoupling layers limiting the detrimental interactions between these molecules and the bottom electrode.

METHODS

Synthesis. Hqnal and $[\text{Fe}(\text{qnal})_2] \cdot \text{CH}_2\text{Cl}_2$ were synthesized according to the literature procedures.^{22,23} The ^{57}Fe isotopically enriched $[\text{}^{57}\text{Fe}(\text{qnal})_2] \cdot \text{CH}_2\text{Cl}_2$ has been prepared according to the procedure used for $[\text{Fe}(\text{qnal})_2] \cdot \text{CH}_2\text{Cl}_2$ using $^{57}\text{FeCl}_2$ prepared starting from metallic Fe with an 87% isotopic enrichment in ^{57}Fe (see Supporting Information). All other reagents were purchased and used as received. All manipulations were performed under a N_2 inert atmosphere to avoid oxidation of the Fe(II) salt before complexation. The complete description of the synthetic procedures for both $[\text{Fe}(\text{qnal})_2]$ and $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ are reported in Supporting Information (see Figure S1-S2). PXRD confirmed that the two complexes are perfectly isostructural (Figure S2 in Supporting Information)

Bulk magnetic measurements. Magnetization measurements were performed in direct current (DC) scan mode in the 5–300 K temperature range with a scan rate of 2 K/min and with an applied magnetic field of 1.0 T on powdered samples of $[\text{Fe}(\text{qnal})_2] \cdot \text{CH}_2\text{Cl}_2$ and $[\text{}^{57}\text{Fe}(\text{qnal})_2] \cdot \text{CH}_2\text{Cl}_2$ using a Quantum Design Magnetic Properties Measurement System (MPMS) magnetometer equipped with Superconducting Quantum Interference Device (SQUID) (Figure S2). Magnetization data were corrected for the TeflonTM sample holder and for the diamagnetic contribution as deduced by using Pascal's constants table.³⁹

Standard transmission Mössbauer characterization. Preliminary Mössbauer measurements on a powder sample of $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ were performed by means of a standard Mössbauer setup in transmission geometry. Mössbauer spectra were collected by means of a Kr-CO₂ proportional counter, FastTM electronics for gamma ray spectroscopy and a WisselTM spectrometer, which was run in sinusoidal acceleration mode ($v_{\text{max}} = 2.7 \text{ mm/s}$ or 4.0 mm/s) and calibrated by using a standard metal iron foil. Measurements were carried out between 80 K and 290 K by using a He based OxfordTM flux cryogenic system. The γ -ray source was a 25-mCi ^{57}Co in rhodium matrix with Lamb-Mössbauer factor $f = 0.66$, as measured by applying the method described previously.⁴⁰ The intensity of the radiation on the sample, having a focal spot $\sim 1 \text{ cm}^2$, is of the order of 10^4 photons per second. The sensitivity of the setup is limited to bulk samples.⁴¹ Approximately 20.3 mg/cm^2 of $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ were used for the measurements.

Synchrotron-based Mössbauer characterization. Nanostructured samples of $[\text{}^{57}\text{Fe}(\text{qnal})_2]$ on gold were investigated by the Synchrotron Mössbauer Source (SMS) set up at the Nuclear Resonance⁴² beamline ID18 at the European Synchrotron Radiation Facility (ESRF). Collimation and monochromatization is achieved via a multi-step optics including the nuclear resonant monochromator obtained with a $^{57}\text{FeBO}_3$ single crystal.^{43,44} Full width at half maximum (FWHM) of the ^{57}Fe -resonant line was set at a value approximately three times larger than for a radioactive source (FWHM mean value $\sim 0.34 \text{ mm/s}$), obtaining an intensity of about 1.5×10^4 photons per second. The spot size was *ca.* $18 \text{ }\mu\text{m}$ in both dimensions. The radiation is fully recoilless (it does not contain any background), implying $f \sim 1$. The Mössbauer spectra were recorded by collecting the radiation reflected by the surface in a grazing incidence geometry (about 0.1 degree). This feature, together with the extreme focusing of the beam, provides a thousand-fold amplification factor in the effective thickness (a dimensionless parameter that takes into account the number of

Mössbauer active nuclei encountered by the radiation along its path in the sample) with respect to a standard experiment performed at normal or close to normal incidence. Further details can be found in two recent papers in which some of us exploited SMS for the characterization of molecular ultra-thin layer deposits.^{32,45} Samples for this characterization were a 100 nm film of $[^{57}\text{Fe}(\text{qnal})_2]$ grown on a thick polycrystalline gold film deposited on silicon with a 5 nm Ti adhesion layer (SSENS, Enschede, NL), and as a check against the bulk conventional Mössbauer spectra, a dropcast film of the compound on the same substrate obtained from a dichloromethane solution. The thickness of this sample was evaluated from the effective thickness obtained from the fit of the SMS spectra and comparing it with the one obtained for the 100 nm film (the thickness of the film was determined by AFM). In particular, a ratio of effective thicknesses equal to 3.6 was found, therefore pointing to an average thickness of 320 ± 20 nm for the dropcast. Spectra were measured at different temperatures in the range 3.0 K - 290 K using the superconducting He-exchange gas cryo-magnetic system. For the Light-Induced Excited Spin State Trapping (LIESST) measurements, the sample holder was modified in order to accommodate a couple of InGaAsP LEDs (Roithner LaserTechnik GmbH, nominal optical power = 2 mW with 545 nm nominal wavelength, decreasing to 531 nm at 10 K).

Mössbauer data analysis. The SMS spectra were interpreted by means of a fitting procedure based on the evaluation of the transmission integral function.^{32,45} At each temperature, the absorption cross-section of the sample was considered as the superposition of two contributions associated with an HS and a LS state, characterized by different values of the hyperfine parameters (isomer shift δ and quadrupole splitting ΔE_Q). Moreover, Gaussian distributions of the LS and HS quadrupole splitting were supposed. A proper fitting of the dropcast and sublimated sample required to include impurity species. Their contribution to the spectra is of the order of 10 % and

20 % for the dropcast and 100 nm thick sample, respectively. The same fitting procedure was used to interpret the spectra of the bulk sample measured with standard Mössbauer spectroscopy, except for replacing in the transmission integral function the line shape of the source and the sample effective thickness with those of the standard Mössbauer setup.³² The core of the fitting procedure is represented by the LMDIF routine of the MinPack library (www.netlib.org). Moreover, the standard deviations on the fit parameters are evaluated from the diagonal terms of the variance-covariance matrix, which is a fit procedure output.

Electrochemical analysis. The electrochemical experiments were carried out using an Autolab PGSTAT101 potentiostat. The experiments were performed under an inert atmosphere of argon using a three-electrode configuration in a single compartment cell. The electrodes consisted of a platinum disc as working electrode, a silver wire coated with silver chloride as reference electrode, and a platinum wire as counter electrode. A 0.1 M solution of *n*Bu₄PF₆ (Fluka, electrochemical grade) in dichloromethane (Honeywell Riedel-de Haën, *purissimum*) was used as supporting electrolyte. Standard cyclic voltammetry experiments (Figure S5) and square wave voltammetry experiments (Figure S5) were performed at 25, 50, 100, and 200 mV s⁻¹, and were done both with and without ferrocene as an internal reference. The potentials are quoted versus the Fc/Fc⁺ redox couple. For the estimation of the ionization potentials, we used the literature value $E_{1/2}(\text{Fc}/\text{Fc}^+) = 0.640 \text{ V vs. NHE}$.

Theoretical modelling. The orbital energies were estimated from density functional theory calculations with the Gaussian09⁴⁶ program using the restricted and unrestricted B3LYP functionals^{47–50} for the low spin and high spin complexes, respectively. The geometry of the complexes were first pre-optimized with the LanL2DZ basis set,^{51–54} followed by a geometry

optimization with the 6-31G(d,p) basis set,^{55–58} and finally single point energy calculations were performed with the 6-31++G(d,p) basis set.⁵⁹

Device preparation. Ultraflat Ag metal stripes were prepared using a combination of a standard lift-off and template stripping processes. A 300 nm thick layer of LOR-3B lift-off resin (Microchem) was spin-coated on a high-quality Si (100) wafer (WAS4P1020, Neyco) at 3000 rpm for 45 s, and the wafer was subsequently baked at 180°C for 15 min. A 2 μ m thick layer of positive photoresist (S1818, Shipley) was then spin-coated on top of the LOR3B at 4000 rpm for 30 s and the wafer was then baked at 115°C for 60 s. The resist was then exposed through a high-resolution soft photomask (Selba) with a UV-Kub 2 (Kloe) LED exposure tool (8 s at 100% power) and developed in MF-319 (Microposit) for 40 s under gentle agitation. The developed wafer was then rinsed carefully with deionized water and dried under a stream of nitrogen. After drying, it was de-scummed with an air plasma for 5 minutes (Harrick Plasma). 200 nm of silver was then evaporated on top of the patterned wafers with a thermal evaporator (Plassys) at a rate of 1-2 Å/s, and the lift-off was performed in acetone with gentle agitation until complete removal of the unwanted metallic film, and the excess LOR-3B resist was removed by gentle agitation in MF-319. To allow for an easy peeling of the stripes, we modified the SiO_x, selectively, by vapor silanization with a fluorosilane (1H,1H,2H,2H-perfluorooctyl-trichlorosilane, Sigma-Aldrich) (see the processing scheme in Figure S6 in Supporting Information). We cast a UV-curable optical adhesive (OA, NOA 61, Norland) to glue the stripes to a glass chip, and after UV exposure we cleaved the Ag/adhesive/glass composite from the wafer to obtain the array of electrodes. The molecular sublimations were performed in a homemade effusion cell. A crucible was filled with the powder of [Fe(qnal)₂] \cdot CH₂Cl₂ and once the pressure reached the 10⁻⁷ mbar range, the temperature was gently raised up to the sublimation temperature. The deposition rate was

monitored by a quartz microbalance (QCM) and stabilized in the 0.4 nm/h range at a temperature of 570 K. The QCM calibration was determined by the deposition of a 50 nm thick film of $[\text{Fe}(\text{qnal})_2]$ on an ultra-flat silicon wafer through a patterned TEM grid, and by evaluating the thickness of the unmasked area of that film *ex situ* (Figure S6) by an NTMDT P47-pro AFM setup equipped with NSC36 micromash tips. The vertical device was finalized (Figure S7) by evaporating 40 nm of $[\text{Fe}(\text{qnal})_2]$ on top of 50 μm wide template-stripped Ag wires (obtained as described above), a subsequent evaporation of 10 nm of LiF, deposited using an e-beam heated cell, above which a gold crossbar (width ca. 250 μm and height ca. 35 nm) was realized with the evaporation through a metallic mask.

FIB-STEM analysis. TEM lamella preparation and STEM characterization methodologies were used to acquire a stratigraphic profile of the device, thus enabling to check its architecture (thickness and roughness of the layers). Lamella preparation and STEM analysis were performed in a single workflow, using a TESCAN GAIA 3 FIB/SEM. The microscope, located at the Electron Microscopy Facility (CE.M.E.) of the CNR in Florence, is equipped with a Triglav Electron Column and a Cobra Ga Ion Column. An $8 \times 4 \times 1 \mu\text{m}^3$ lamella (length \times depth \times thickness) was extracted from the surface of one of the complete devices; the lamella was then thinned down to less than 40 nm, prior to the characterization by the built-in STEM detector. STEM images were analyzed with the software Gwyddion⁶⁰ determining the thicknesses of the layers measuring, within the experimental error, the distances between contiguous inflection points in the vertical intensity profiles.

Transport measurements. Electric transport measurements on devices were performed employing a home-made cabled sample-holder in order to place the sample inside a PPMS

(Quantum Design) which allowed the control of the sample temperature. Gold wires and conductive silver paint were used for electric connections of the samples. I-V measurements were performed at different temperatures in the range 135 – 310 K making use of a source-meter unit (Keithley SMU 2601) to supply voltages (in the range 0 – 1 V) while the currents were measured with an electrometer (Keithley 6514) in a 2-wire configuration.

ASSOCIATED CONTENT

Supporting Information. The Supporting Information is available free of charge on the ACS Publications website. Additional characterization data are present: Synthesis, Bulk magnetic and Powder XRD spectra, AFM images, Device preparation, Mössbauer characterization, Voltammetric data, and electric transport characterization.

Corresponding Author

*Correspondence should be addressed to Dr. Giuseppe Cucinotta (giuseppe.cucinotta@unifi.it) and Dr. Lorenzo Poggini (lorenzo.poggini@unifi.it)

Present Addresses

† [Matteo Atzori, Laboratoire National des Champs Magnétiques Intenses (LNCMI), CNRS – 25 avenue des Martyrs, 38042 – Grenoble (France)]

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript. ‡These authors contributed equally. NG and MA synthesized

the molecular system and their ^{57}Fe enriched analogue. MG performed the DFT calculations and CV measurements and prepared the template-stripped Ag substrates, LP, AC, AIC, RR, PR and MM participated to the SMS experiments, AC and MF performed the standard MB experiments and carried out the MB and SMS data analysis. EB and AL executed the FIB-STEM characterization, LP assembled the vertical hybrid device and GC performed the transport measurements and data analysis. MM coordinated the experiments.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENT

We acknowledge Prof. Gabriele Spina at University of Florence for his help in Mössbauer data analysis. We acknowledge the European Synchrotron Radiation Facility (Grenoble, France) for provision of synchrotron radiation resources at the Nuclear Resonance beamline ID18 during CH-4909 beamtime. We are grateful to Jean-Philippe Celse at the ESRF for providing assistance in using beamline ID18. This work was supported by Fondazione CR Firenze (through Spin-E project n. 2017.0730 coordinated by MM and through the grant for MF, project n. 2016.1104), the Italian MIUR (“Progetto Dipartimenti di Eccellenza 2018-2022, ref. B96C1700020008” allocated to Department of Chemistry “Ugo Schiff”), the French National Research Agency (ANR) Investment for the Future Programme IdEx Bordeaux (ANR-10-IDEX-03-02, grants for MG and LP), FEMTOMAT project (ANR-13-BS04-002, PR) for the economic support. AL and EB acknowledge “Fondazione Cassa di Risparmio di Firenze” and Regione Toscana for the

project FELIX (POR FESR 2014-2020, grant number no. 6455) for financial support given for the acquisition of the TESCAN GAIA3 electron microscope.

REFERENCES

- (1) Heath, J. R.; Ratner, M. A. Molecular Electronics. *Phys. Today* **2003**, *56* (5), 43–49. <https://doi.org/10.1063/1.1583533>.
- (2) Xin, N.; Guan, J.; Zhou, C.; Chen, X.; Gu, C.; Li, Y.; Ratner, M. A.; Nitzan, A.; Stoddart, J. F.; Guo, X. Concepts in the Design and Engineering of Single-Molecule Electronic Devices. *Nat. Rev. Phys.* **2019**, *1* (3), 211–230. <https://doi.org/10.1038/s42254-019-0022-x>.
- (3) Vilan, A.; Aswal, D.; Cahen, D. Large-Area, Ensemble Molecular Electronics: Motivation and Challenges. *Chem. Rev.* **2017**, *117* (5), 4248–4286. <https://doi.org/10.1021/acs.chemrev.6b00595>.
- (4) Kim, D.; Jeong, H.; Hwang, W. T.; Jang, Y.; Sysoiev, D.; Scheer, E.; Huhn, T.; Min, M.; Lee, H.; Lee, T. Reversible Switching Phenomenon in Diarylethene Molecular Devices with Reduced Graphene Oxide Electrodes on Flexible Substrates. *Adv. Funct. Mater.* **2015**, *25* (37), 5918–5923. <https://doi.org/10.1002/adfm.201502312>.
- (5) Bhimanapati, G. R.; Lin, Z.; Meunier, V.; Jung, Y.; Cha, J.; Das, S.; Xiao, D.; Son, Y.; Strano, M. S.; Cooper, V. R.; Liang, L.; Louie, S. G.; Ringe, E.; Zhou, W.; Kim, S. S.; Naik, R. R.; Sumpter, B. G.; Terrones, H.; Xia, F.; Wang, Y.; Zhu, J.; Akinwande, D.; Alem, N.; Schuller, J. A.; Schaak, R. E.; Terrones, M.; Robinson, J. A. Recent Advances in Two-

- Dimensional Materials beyond Graphene. *ACS Nano* **2015**, *9* (12), 11509–11539. <https://doi.org/10.1021/acsnano.5b05556>.
- (6) Molnár, G.; Rat, S.; Salmon, L.; Nicolazzi, W.; Bousseksou, A. Spin Crossover Nanomaterials: From Fundamental Concepts to Devices. *Adv. Mater.* **2018**, *30* (5), 1703862. <https://doi.org/10.1002/adma.201703862>.
- (7) Bartual-Murgui, C.; Akou, A.; Thibault, C.; Molnár, G.; Vieu, C.; Salmon, L.; Bousseksou, A. Spin-Crossover Metal–Organic Frameworks: Promising Materials for Designing Gas Sensors. *J. Mater. Chem. C* **2015**, *3* (6), 1277–1285. <https://doi.org/10.1039/C4TC02441A>.
- (8) Linares, J.; Codjovi, E.; Garcia, Y. Pressure and Temperature Spin Crossover Sensors with Optical Detection. *Sensors* **2012**, *12* (12), 4479–4492. <https://doi.org/10.3390/s120404479>.
- (9) Ruiz, E. Charge Transport Properties of Spin Crossover Systems. *Phys. Chem. Chem. Phys.* **2014**, *16* (1), 14–22. <https://doi.org/10.1039/c3cp54028f>.
- (10) Lefter, C.; Rat, S.; Costa, J. S.; Manrique-Juárez, M. D.; Quintero, C. M.; Salmon, L.; Séguy, I.; Leichle, T.; Nicu, L.; Demont, P.; Rotaru, A.; Molnár, G.; Bousseksou, A. Current Switching Coupled to Molecular Spin-States in Large-Area Junctions. *Adv. Mater.* **2016**, *28* (34), 7508–7514. <https://doi.org/10.1002/adma.201601420>.
- (11) Senthil Kumar, K.; Ruben, M. Emerging Trends in Spin Crossover (SCO) Based Functional Materials and Devices. *Coord. Chem. Rev.* **2017**, *346*, 176–205. <https://doi.org/10.1016/j.ccr.2017.03.024>.
- (12) Poggini, L.; Gonidec, M.; González-Estefan, J. H. J. H.; Pecastaings, G.; Gobaut, B.; Rosa,

- P.; González-Estefan, J. H.; Pecastaings, G.; Gobaut, B.; Rosa, P. Vertical Tunnel Junction Embedding a Spin Crossover Molecular Film. *Adv. Electron. Mater.* **2018**, *1800204* (12), 1800204. <https://doi.org/10.1002/aelm.201800204>.
- (13) Poggini, L.; Gonidec, M.; Canjeevaram Balasubramanyam, R. K.; Squillantini, L.; Pecastaings, G.; Caneschi, A.; Rosa, P. Temperature-Induced Transport Changes in Molecular Junctions Based on a Spin Crossover Complex. *J. Mater. Chem. C* **2019**, *7*, 5343–5347. <https://doi.org/10.1039/c8tc06587j>.
- (14) Ruben, M.; Kumar, K. S. Sublimable Spin Crossover Complexes: From Spin-State Switching to Molecular Devices. *Angew. Chemie Int. Ed.* **2019**. <https://doi.org/10.1002/anie.201911256>.
- (15) Lefter, C.; Davesne, V.; Salmon, L.; Molnár, G.; Demont, P.; Rotaru, A.; Bousseksou, A. Charge Transport and Electrical Properties of Spin Crossover Materials: Towards Nanoelectronic and Spintronic Devices. *Magnetochemistry* **2016**, *2* (1), 18. <https://doi.org/10.3390/magnetochemistry2010018>.
- (16) Cinchetti, M.; Dediu, V. A.; Hueso, L. E. Activating the Molecular Spinterface. *Nat. Mater.* **2017**, *16* (5), 507–515. <https://doi.org/10.1038/nmat4902>.
- (17) Chiechi, R. C.; Weiss, E. A.; Dickey, M. D.; Whitesides, G. M. Eutectic Gallium-Indium (EGaIn): A Moldable Liquid Metal for Electrical Characterization of Self-Assembled Monolayers. *Angew. Chemie - Int. Ed.* **2008**, *47* (1), 142–144. <https://doi.org/10.1002/anie.200703642>.
- (18) Atzori, M.; Poggini, L.; Squillantini, L.; Cortigiani, B.; Gonidec, M.; Bencok, P.; Sessoli,

- R.; Mannini, M. Thermal and Light-Induced Spin Transition in a Nanometric Film of a New High-Vacuum Processable Spin Crossover Complex. *J. Mater. Chem. C* **2018**, 6 (33), 8885–8889. <https://doi.org/10.1039/C8TC02685H>.
- (19) Prada, S.; Martinez, U.; Pacchioni, G. Work Function Changes Induced by Deposition of Ultrathin Dielectric Films on Metals: A Theoretical Analysis. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2008**, 78 (23), 235423. <https://doi.org/10.1103/PhysRevB.78.235423>.
- (20) Braun, S.; Salaneck, W. R.; Fahlman, M. Energy-Level Alignment at Organic/Metal and Organic/Organic Interfaces. *Advanced Materials*. John Wiley & Sons, Ltd April 20, 2009, pp 1450–1472. <https://doi.org/10.1002/adma.200802893>.
- (21) Lampert, M. A. Volume-Controlled Current Injection in Insulators. *Reports Prog. Phys.* **1964**, 27 (1), 329–367. <https://doi.org/10.1088/0034-4885/27/1/307>.
- (22) Tisato, F.; Refosco, F.; Moresco, A.; Bandoli, G.; Mazzi, U.; Nicolini, M. Synthesis and Characterization of Technetium(V) and Rhenium(V) Oxo-Complexes with Schiff-Base Ligands Containing the ONN Donor-Atom Set. Molecular Structure of Trans-Dichloro-Oxo[1-(8'-Quinolyliminomethyl)-2-Naphtholato-NN'O] Technetium(V). *J. Chem. Soc. Dalt. Trans.* **1990**, No. 7, 2225–2232. <https://doi.org/10.1039/DT9900002225>.
- (23) Kuroda-Sowa, T.; Yu, Z.; Senzaki, Y.; Sugimoto, K.; Maekawa, M.; Munakata, M.; Hayami, S.; Maeda, Y. Abrupt Spin Transitions and LIESST Effects Observed in FeII Spin-Crossover Complexes with Extended π -Conjugated Schiff-Base Ligands Having N4O2 Donor Sets. *Chem. Lett.* **2008**, 37 (12), 1216–1217. <https://doi.org/10.1246/cl.2008.1216>.
- (24) Phan, H.; Hrudka, J. J.; Igimbayeva, D.; Lawson Daku, L. M.; Shatruk, M. A Simple

- Approach for Predicting the Spin State of Homoleptic Fe(II) Tris-Diimine Complexes. *J. Am. Chem. Soc.* **2017**, *139* (18), 6437–6447. <https://doi.org/10.1021/jacs.7b02098>.
- (25) Atzori, M.; Artizzu, F. *Functional Molecular Materials An Introductory Textbook*; Pan Stanford, 2018.
- (26) Poggini, L.; Londi, G.; Milek, M.; Naim, A.; Lanzilotto, V.; Cortigiani, B.; Bondino, F.; Magnano, E.; Otero, E.; Saintavit, P.; Arrio, M.-A.; Juhin, A.; Marchivie, M.; Khusniyarov, M. M.; Totti, F.; Rosa, P.; Mannini, M. Surface Effects on a Photochromic Spin-Crossover Iron(II) Molecular Switch Adsorbed on Highly Oriented Pyrolytic Graphite. *Nanoscale* **2019**. <https://doi.org/10.1039/C9NR05947D>.
- (27) Gopakumar, T. G.; Bernien, M.; Naggert, H.; Matino, F.; Hermanns, C. F.; Bannwarth, A.; Mühlenberend, S.; Krüger, A.; Krüger, D.; Nickel, F.; Walter, W.; Berndt, R.; Kuch, W.; Tuczek, F. Spin-Crossover Complex on Au(111): Structural and Electronic Differences between Mono- and Multilayers. *Chem. - A Eur. J.* **2013**, *19* (46), 15702–15709. <https://doi.org/10.1002/chem.201302241>.
- (28) Ossinger, S.; Naggert, H.; Kipgen, L.; Jasper-Toennies, T.; Rai, A.; Rudnik, J.; Nickel, F.; Arruda, L. M.; Bernien, M.; Kuch, W.; Berndt, R.; Tuczek, F. Vacuum-Evaporable Spin-Crossover Complexes in Direct Contact with a Solid Surface: Bismuth versus Gold. *J. Phys. Chem. C* **2017**, *121* (2), 1210–1219. <https://doi.org/10.1021/acs.jpcc.6b10888>.
- (29) Atzori, M.; Poggini, L.; Squillantini, L.; Cortigiani, B.; Gonidec, M.; Bencok, P.; Sessoli, R.; Mannini, M. Thermal and Light-Induced Spin Transition in a Nanometric Film of a New High-Vacuum Processable Spin Crossover Complex. *J. Mater. Chem. C* **2018**, *6* (33).

<https://doi.org/10.1039/c8tc02685h>.

- (30) Ossinger, S.; Näther, C.; Buchholz, A.; Schmidtman, M.; Mangelsen, S.; Beckhaus, R.; Plass, W.; Tuczek, F. Spin Transition of an Iron(II) Organoborate Complex in Different Polymorphs and in Vacuum-Deposited Thin Films: Influence of Cooperativity. *Inorg. Chem.* **2020**, acs.inorgchem.9b03354. <https://doi.org/10.1021/acs.inorgchem.9b03354>.
- (31) Poggini, L.; Milek, M.; Londi, G.; Naim, A.; Poneti, G.; Squillantini, L.; Magnani, A.; Totti, F.; Rosa, P.; Khusniyarov, M. M.; Mannini, M. Room Temperature Control of Spin States in a Thin Film of a Photochromic Iron(II) Complex. *Mater. Horizons* **2018**, 5 (3), 506–513. <https://doi.org/10.1039/c7mh01042g>.
- (32) Cini, A.; Poggini, L.; Chumakov, A. I.; Rüffer, R.; Spina, G.; Wattiaux, A.; Duttine, M.; Gonidec, M.; Fittipaldi, M.; Rosa, P.; Mannini, M. Synchrotron-Based Mössbauer Spectroscopy Characterization of Sublimated Spin Crossover Molecules. *Phys. Chem. Chem. Phys.* **2020**, 22 (12), 6626–6637. <https://doi.org/10.1039/c9cp04464g>.
- (33) Koopmans, T. Über Die Zuordnung von Wellenfunktionen Und Eigenwerten Zu Den Einzelnen Elektronen Eines Atoms. *Physica* **1934**, 1 (1–6), 104–113. [https://doi.org/10.1016/S0031-8914\(34\)90011-2](https://doi.org/10.1016/S0031-8914(34)90011-2).
- (34) Nijhuis, C. A.; Reus, W. F.; Whitesides, G. M. Mechanism of Rectification in Tunneling Junctions Based on Molecules with Asymmetric Potential Drops. *J. Am. Chem. Soc.* **2010**, 132 (51), 18386–18401. <https://doi.org/10.1021/ja108311j>.
- (35) He, J.; Armstrong, J.; Cong, P.; Menagen, B.; Igaher, L.; Beale, A. M.; Etgar, L.; Avnir, D. Affecting an Ultra-High Work Function of Silver. *Angew. Chemie Int. Ed.* **2020**, 59 (12),

- 4698–4704. <https://doi.org/10.1002/anie.201912293>.
- (36) Weiss, E. A.; Kaufman, G. K.; Kriebel, J. K.; Li, Z.; Schalek, R.; Whitesides, G. M. Si/SiO₂-Templated Formation of Ultraflat Metal Surfaces on Glass, Polymer, and Solder Supports: Their Use as Substrates for Self-Assembled Monolayers. *Langmuir* **2007**, *23* (19), 9686–9694. <https://doi.org/10.1021/la701919r>.
- (37) Rose, A. Space-Charge-Limited Currents in Solids. *Phys. Rev.* **1955**, *97* (6), 1538–1544. <https://doi.org/10.1103/PhysRev.97.1538>.
- (38) Mott, N. F.; Gurney, R. W. *Electronic Processes in Ionic Crystals*, 2d ed.; Clarendon Press: Oxford, 1948.
- (39) Bain, G. A.; Berry, J. F. Diamagnetic Corrections and Pascal's Constants. *J. Chem. Educ.* **2008**, *85* (4), 532. <https://doi.org/10.1021/ed085p532>.
- (40) Spina, G.; Lantieri, M. A Straightforward Experimental Method to Evaluate the Lamb-Mössbauer Factor of a ⁵⁷Co/Rh Source. *Nucl. Instruments Methods Phys. Res. Sect. B Beam Interact. with Mater. Atoms* **2014**, *318* (PART B), 253–257. <https://doi.org/10.1016/j.nimb.2013.10.002>.
- (41) Gütlich, P.; Bill, E. (Eckhard); Trautwein, A. *Mossbauer Spectroscopy and Transition Metal Chemistry: Fundamentals and Application*; Springer, 2011.
- (42) Rüffer, R.; Chumakov, A. I. Nuclear Resonance Beamline at ESRF. *Hyperfine Interact.* **1996**, *97–98* (1), 589–604. <https://doi.org/10.1007/BF02150199>.
- (43) Smirnov, G. V; van Bürck, U.; Chumakov, A. I.; Baron, A. Q. R.; Rüffer, R. Synchrotron

- Mössbauer Source. *Phys. Rev. B* **1997**, *55* (9), 5811–5815.
<https://doi.org/10.1103/PhysRevB.55.5811>.
- (44) Potapkin, V.; Chumakov, A. I.; Smirnov, G. V.; Celse, J. P.; Rüffer, R.; McCammon, C.; Dubrovinsky, L. The ^{57}Fe Synchrotron Mössbauer Source at the ESRF. *J. Synchrotron Radiat.* **2012**, *19* (4), 559–569. <https://doi.org/10.1107/S0909049512015579>.
- (45) Cini, A.; Mannini, M.; Totti, F.; Fittipaldi, M.; Spina, G.; Chumakov, A.; Rüffer, R.; Cornia, A.; Sessoli, R. Mössbauer Spectroscopy of a Monolayer of Single Molecule Magnets. *Nat. Commun.* **2018**, *9* (1), 1–9. <https://doi.org/10.1038/s41467-018-02840-w>.
- (46) Frisch, M. J.; Trucks, G. W.; Schlegel, H. B.; Scuseria, G. E.; Robb, M. A.; Cheeseman, J. R.; Scalmani, G.; Barone, V.; Mennucci, B.; Petersson, G. A.; Nakatsuji, H.; Caricato, M.; Li, X.; Hratchian, H. P.; Izmaylov, A. F.; Bloino, J.; Zheng, G.; Sonnenberg, J. L.; Hada, M.; Ehara, M.; Toyota, K.; Fukuda, R.; Hasegawa, J.; Ishida, M.; Nakajima, T.; Honda, Y.; Kitao, O.; Nakai, H.; Vreven, T.; Montgomery, J. A.; Peralta, J. E.; Ogliaro, F.; Bearpark, M.; Heyd, J. J.; Brothers, E.; Kudin, K. N.; Staroverov, V. N.; Kobayashi, R.; Normand, J.; Raghavachari, K.; Rendell, A.; Burant, J. C.; Iyengar, S. S.; Tomasi, J.; Cossi, M.; Rega, N.; Millam, J. M.; Klene, M.; Knox, J. E.; Cross, J. B.; Bakken, V.; Adamo, C.; Jaramillo, J.; Gomperts, R.; Stratmann, R. E.; Yazyev, O.; Austin, A. J.; Cammi, R.; Pomelli, C.; Ochterski, J. W.; Martin, R. L.; Morokuma, K.; Zakrzewski, V. G.; Voth, G. A.; Salvador, P.; Dannenberg, J. J.; Dapprich, S.; Daniels, A. D.; Farkas; Foresman, J. B.; Ortiz, J. V.; Cioslowski, J.; Fox, D. J. Gaussian 09, Revision A.02. *Gaussian 09, Revision A02*, Gaussian, Inc., Wallingford CT. 2009.
- (47) Becke, A. D. Density-Functional Exchange-Energy Approximation with Correct

- Asymptotic Behavior. *Phys. Rev. A* **1988**, 38 (6), 3098–3100.
<https://doi.org/10.1103/PhysRevA.38.3098>.
- (48) Lee, C.; Yang, W.; Parr, R. G. Development of the Colle-Salvetti Correlation-Energy Formula into a Functional of the Electron Density. *Phys. Rev. B* **1988**, 37 (2), 785–789.
<https://doi.org/10.1103/PhysRevB.37.785>.
- (49) Vosko, S. H.; Wilk, L.; Nusair, M. Accurate Spin-Dependent Electron Liquid Correlation Energies for Local Spin Density Calculations: A Critical Analysis. *Can. J. Phys.* **1980**, 58 (8), 1200–1211. <https://doi.org/10.1139/p80-159>.
- (50) Stephens, P. J.; Devlin, F. J.; Chabalowski, C. F.; Frisch, M. J. Ab Initio Calculation of Vibrational Absorption and Circular Dichroism Spectra Using Density Functional Force Fields. *J. Phys. Chem.* **1994**, 98 (45), 11623–11627. <https://doi.org/10.1021/j100096a001>.
- (51) Dunning, T. H.; Hay, P. J. Gaussian Basis Sets for Molecular Calculations. In *Methods of Electronic Structure Theory*; Springer US: Boston, MA, 1977; pp 1–27.
https://doi.org/10.1007/978-1-4757-0887-5_1.
- (52) Hay, P. J.; Wadt, W. R. Ab Initio Effective Core Potentials for Molecular Calculations. Potentials for the Transition Metal Atoms Sc to Hg. *J. Chem. Phys.* **1985**, 82 (1), 270–283.
<https://doi.org/10.1063/1.448799>.
- (53) Wadt, W. R.; Hay, P. J. Ab Initio Effective Core Potentials for Molecular Calculations. Potentials for Main Group Elements Na to Bi. *J. Chem. Phys.* **1985**, 82 (1), 284–298.
<https://doi.org/10.1063/1.448800>.

- (54) Hay, P. J.; Wadt, W. R. Ab Initio Effective Core Potentials for Molecular Calculations. Potentials for K to Au Including the Outermost Core Orbitals. *J. Chem. Phys.* **1985**, *82* (1), 299–310. <https://doi.org/10.1063/1.448975>.
- (55) Binning, R. C.; Curtiss, L. A. Compact Contracted Basis Sets for Third-Row Atoms: Ga–Kr. *J. Comput. Chem.* **1990**, *11* (10), 1206–1216. <https://doi.org/10.1002/jcc.540111013>.
- (56) Blaudeau, J.-P.; McGrath, M. P.; Curtiss, L. A.; Radom, L. Extension of Gaussian-2 (G2) Theory to Molecules Containing Third-Row Atoms K and Ca. *J. Chem. Phys.* **1997**, *107* (13), 5016–5021. <https://doi.org/10.1063/1.474865>.
- (57) Rassolov, V. A.; Pople, J. A.; Ratner, M. A.; Windus, T. L. 6-31G * Basis Set for Atoms K through Zn. *J. Chem. Phys.* **1998**, *109* (4), 1223–1229. <https://doi.org/10.1063/1.476673>.
- (58) Rassolov, V. A.; Ratner, M. A.; Pople, J. A.; Redfern, P. C.; Curtiss, L. A. 6-31G* Basis Set for Third-Row Atoms. *J. Comput. Chem.* **2001**, *22* (9), 976–984. <https://doi.org/10.1002/jcc.1058>.
- (59) Frisch, M. J.; Pople, J. A.; Binkley, J. S. Self-consistent Molecular Orbital Methods 25. Supplementary Functions for Gaussian Basis Sets. *J. Chem. Phys.* **1984**, *80* (7), 3265–3269. <https://doi.org/10.1063/1.447079>.
- (60) Nečas, D.; Klapetek, P. Gwyddion: An Open-Source Software for SPM Data Analysis. *Central European Journal of Physics*. February 2012, pp 181–188. <https://doi.org/10.2478/s11534-011-0096-2>.

TABLE OF CONTENTS

