

Article published in *ACS Nano* (2015) 9, 3385–3396

DOI: 10.1021/nn5070953

<https://pubs.acs.org/doi/10.1021/nn5070953>


High Relaxivity Gd(III)-DNA Gold Nanostars: Investigation of Shape Effects on Proton Relaxation

Matthew W. Rotz,[§] Kayla S. B. Culver,[†] Giacomo Parigi,[‡] Keith W. MacRenaris,[‡] Claudio Luchinat,[‡] Teri W. Odom,[†] Thomas J. Meade^{§,*}

[†]Departments of Chemistry, Materials Science and Engineering, [§]Departments of Chemistry, Molecular Biosciences, Neurobiology and Radiology, [‡]Quantitative Bio-elemental Imaging Center, Department of Molecular Biosciences, Northwestern University, 2145 Sheridan Road, Evanston, Illinois 60208, United States and [‡]Magnetic Resonance Center (CERM) and Department of Chemistry, University of Florence, Via Luigi Sacconi 6, 50019 Sesto Fiorentino, Italy

Address correspondence to tmeade@northwestern.edu

ABSTRACT

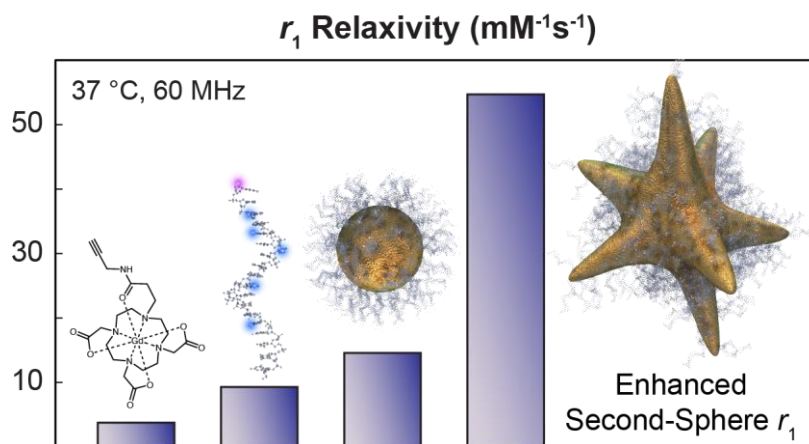

Gadolinium(III) nanoconjugate contrast agents (CAs) have distinct advantages relative to their small molecule counterparts in magnetic resonance imaging (MRI). In addition to increased

Gd(III) payload, a significant improvement in contrast enhancement efficiency, or relaxivity (r_1) is often observed. In this work, we describe the synthesis and characterization of a new class of nanoconjugate CAs, created by covalent attachment of Gd(III) to thiolated DNA (Gd(III)-DNA), followed by surface conjugation onto gold nanostars (DNA-Gd@stars). These conjugates exhibit remarkable r_1 with values up to $98 \text{ mM}^{-1} \text{ s}^{-1}$. Additionally, DNA-Gd@stars show efficient Gd(III) delivery and biocompatibility *in vitro* and generate increased contrast enhancement when imaged at 7 T. Using nuclear magnetic relaxation dispersion (NMRD) analysis, we attribute the high performance of the DNA-Gd@stars to an increased contribution of second-sphere relaxivity compared to that of spherical CA equivalents (DNA-Gd@spheres). Importantly, the surface of the gold nanostar contains Gd(III)-DNA in regions positive, negative, and neutral curvature. We hypothesize that the proton relaxation enhancement observed results from the presence of a unique hydrophilic environment produced by Gd(III)-DNA in these regions, which allows second-sphere water molecules to remain adjacent to Gd(III) ions for up to ten times longer than diffusion. Therefore, this work establishes that particle shape is an important consideration in the design of Gd(III) nanoconjugate CAs.

KEYWORDS: gadolinium; magnetic resonance; nanostar; relaxivity; second-sphere; contrast agent; nuclear magnetic resonance dispersion

MRI is considered an integral part of medical diagnostic imaging due to its high spatiotemporal resolution, excellent soft tissue contrast, and exceptional safety profile.²⁻⁴ Using this technique, high-resolution anatomical images can be obtained without radioactive tracers or ionizing radiation. When native contrast is insufficient for definitive detection, CAs are used to differentiate among areas where specific anatomical detail is difficult to resolve. To address this

shortcoming, paramagnetic chelates of Gd(III) are used to shorten the longitudinal relaxation times (T_1) of proximal water protons in regions of agent accumulation, and thereby generate positive image contrast.⁵ However, due to the relatively low sensitivity of clinically approved small molecule agents, applications are limited because high doses are often required (mM for Gd(III) complexes). To increase the utility of magnetic resonance (MR) CAs, current work has focused on developing strategies for specific delivery (greater accumulation of Gd(III) at the site of interest), and greater proton relaxation efficiency (improved r_1 relaxivity).

Optimizing CA Performance The Solomon Bloembergen Morgen (SBM) theory of relaxivity describes three primary ways in which a Gd(III) agent can be optimized: i) changing the rotational correlation time, τ_r , ii) increasing the rate of water exchange with the lanthanide (the inverse of the inner-sphere water exchange rate, $1/k_{ex}$, or τ_m), and iii) increasing the number of coordinated water molecules, q .⁶⁻⁸ Despite numerous examples of Gd(III) chelates bearing increased values of q to augment r_1 , most CA research focuses on complexes wherein $q = 1$.^{9, 10}

Improving r_1 by Optimizing τ_r Of the aforementioned parameters used to increase r_1 , the most commonly applied is modulation of τ_r . [Increasing this correlation time \(by slowing the Gd\(III\) reorientation time\) is known to improve CA \$r_1\$ significantly at magnetic field strengths \$\leq 1.5\$ T \(corresponding to proton Larmor frequencies of \$\leq 64\$ MHz\). The effects of changing this parameter at higher field strengths, however, is unsubstantial or sometimes detrimental to CA performance.](#)⁶ Often, increasing τ_r is achieved by immobilization of Gd(III) to a nanoparticle or macromolecule. This approach is particularly common because nanoconjugate CAs are chemically accessible, and couple the tumbling rate of the Gd(III) chelates to that of the much larger species. In addition to increased r_1 , this strategy is beneficial for increased local concentrations of CA (high Gd(III) payload per particle). For this reason, a variety of Gd(III)

nanoconjugate CAs have been described, including agents based on biomacromolecules (proteins and viruses), organic nanoparticles (nanodiamonds, liposomes and polymers), and inorganic nanoparticles (silica, titanium and gold).¹¹⁻²¹

Recently, Gd(III)-DNA was attached to spherical gold nanoparticles, creating Gd(III) enriched DNA gold nanoparticle conjugates (DNA-Gd^{III}@AuNP).²² This nanoconjugate design was particularly effective for cellular MR imaging because DNA-Gd^{III}@AuNPs showed both improved r_1 relaxivity per Gd(III) and higher cellular internalization of Gd(III) relative to their small molecule counterparts. Importantly, the nanoconjugates delivered the expected increase in r_1 by lengthening of τ_r , while maintaining the high stability, nuclease resistance, biocompatibility and efficient cell uptake conferred by the densely packed monolayer of DNA on the gold nanoparticle surface.²³⁻²⁵ Attempts to increase r_1 further by increasing the particle size, however, showed only minor improvement.²²

Improving r_1 by Optimizing τ_m Another commonly used approach for improved r_1 described by SBM theory focuses on the rapid and efficient exchange of water within the inner-sphere of Gd(III) complexes (τ_m), a feature which is critical to the generation of high T_1 contrast.²⁶⁻²⁹ However, SBM simulations suggest that a significant enhancement of r_1 using this strategy is only probable in CAs bearing near optimal values of τ_r , particularly at low field strengths (≤ 1.5 T).³⁰ By virtue of their size, nanoconjugate CAs inherently possess relatively slow tumbling rates. For this reason, improvement of r_1 in nanoconjugate systems, where q is held constant, is readily accessible through the optimization of τ_m .

In Gd(III) CA systems, T_1 proton relaxation is dominated by a dipole-dipole mechanism.³¹ Within the equations that describe this behavior, the correlation time parameter, τ_c , is a field

strength dependent variable which contains features of Gd(III) complexes that can be affected by the coordination environment of the lanthanide. This relationship is described by *eq. 1*,


$$\frac{1}{\tau_c} = \frac{1}{T_{1e}} + \frac{1}{\tau_r} + \frac{1}{\tau_m} \quad (1)$$

where T_{1e} is the electronic spin relaxation time, τ_r is the rotational correlation time and τ_m is the inner-sphere water exchange rate. When τ_c^{-1} is equal to 2π times the proton Larmor frequency, r_1 will be equal to its maximum value achievable at that frequency. Predicting and affecting T_{1e} experimentally is not straightforward, thus, approaches to CA optimization commonly focus on modulation of τ_r and τ_m .³² In nanoconjugate CAs, the particle τ_r often exceeds tens of nanoseconds, and therefore τ_c is dominated by the shorter of T_{1e} or τ_m , or both if of similar length. Typical values of T_{1e} between 0.5-1.5 T are approximately 10 ns. In this range of magnetic field strengths, the optimal τ_m value varies from 20 ns at 0.5 T, to 5 ns at 1.5 T, and therefore an optimized CA will possess a τ_m within this range.³⁰

Gd(III) Nanoconjugates and Second-Sphere Relaxivity The water exchange kinetics of lanthanide complexes is a direct result of the metal-ligand coordination environment. Therefore, improvements to τ_m are readily observed by synthetic modification of the Gd(III)-ligand complex prior to particle conjugation.³³⁻³⁵ Alternately, recent work has suggested that confinement of a CA on or near a nanoparticle or protein surface may affect the diffusion of water in the proximity of the CA, and thereby impact its performance by providing a significant second- and outer-sphere relaxivity enhancement.³⁶ Although second- and outer-sphere contributions to relaxivity are generally considered insignificant due to the high rate of water diffusion past the Gd(III), this phenomenon is sometimes cited to explain unexpectedly high values of r_1 in nanoconjugate systems.^{6, 19, 30, 37, 38}

We predict that this behavior can be affected experimentally by altering the water diffusion adjacent to hydrophilic nanoparticle surfaces, and that this may provide a new design parameter for improved r_1 in Gd(III) nanoconjugate CAs. We hypothesize that nanoconjugate CA surface dynamics can be affected by variation in particle shape, and that this alternation can be used to augment r_1 through the enhancement of second-sphere contributions to CA performance. In support of this rationale, recent work has shown that the surface curvature of irregularly shaped nanoparticles can significantly affect the chemical reactivity of surface ligands.³⁹ In an effort to create a high relaxivity CA, we have examined the effects of particle size and shape within the Gd(III)-DNA gold nanoconjugate platform using gold nanostars to produce DNA-Gd@stars (Scheme 1). Importantly, the nanostar particle surface contains regions of positive, negative, and neutral curvature, and thus we predict a significant effect on the local environment of the surface conjugated Gd(III)-DNA.

Herein, we present the synthesis of a new τ_m -optimized, alkyne-bearing Gd(III) chelate to ensure that r_1 relaxivity is not limited by inner-sphere water exchange.⁴⁰ When the Gd(III)

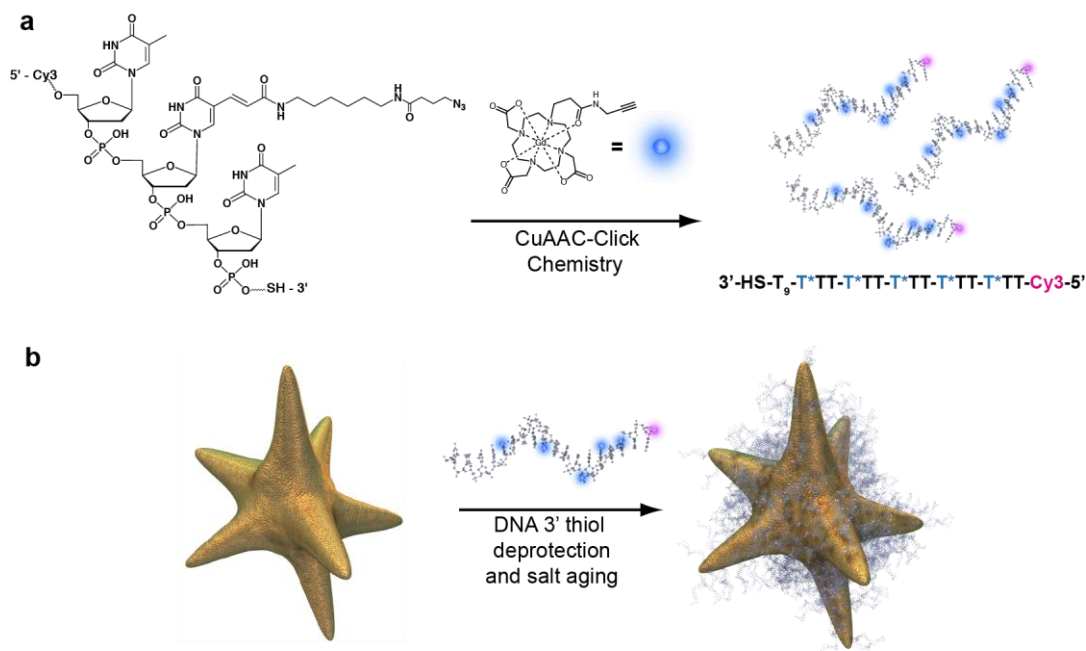


Scheme 1. Preparation of DNA-Gd@stars. (a) A Cy3-labeled 24-mer poly dT oligonucleotide is modified *via* the covalent attachment of Gd(III) to each of 5 azide-bearing dT bases per strand. (b) The functionalized oligonucleotide is deprotected, revealing the 3' thiol and is conjugated to nanostars through a series of increases in salt concentration called salt aging.¹

complex is conjugated to the surface of gold nanostars, DNA-Gd@stars achieve r_1 relaxivities up to $98 \text{ mM}^{-1}\text{s}^{-1}$, a 25-fold greater r_1 relaxivity than FDA-approved chelates at $25 \text{ }^\circ\text{C}$ (32 MHz). Significantly, these values exceed the theoretical maximum relaxivity predicted by SBM theory when a single water molecule is coordinated to the Gd(III) ($q = 1$).³⁰

Employing detailed NMRD analysis, we compare 15-nm DNA-Gd@spheres with the DNA-Gd@stars and demonstrate that their proton relaxation efficiency is the result of optimized inner-sphere water exchange kinetics, and particle surface-mediated elongation of second-sphere water residency lifetimes (and therefore enhanced second-sphere relaxivity).

RESULTS AND DISCUSSION

Synthesis and Characterization of a τ_m -Optimized Gd(III) Complex The water exchange kinetics of lanthanide complexes can be affected by interchange of ligand types or synthetic modifications thereof.⁴¹ Recent work using the macrocyclic ligand [1,4,7-(tris-*tert*-butyl acetate)-1,4,7,10-tetraazacyclododecane], or DO3A, has described a modification shown to increase steric crowding around the water coordination site, thereby shortening τ_m .^{35, 42} Using this previously reported strategy to facilitate an optimal τ_m in our nanoconjugate system, a new

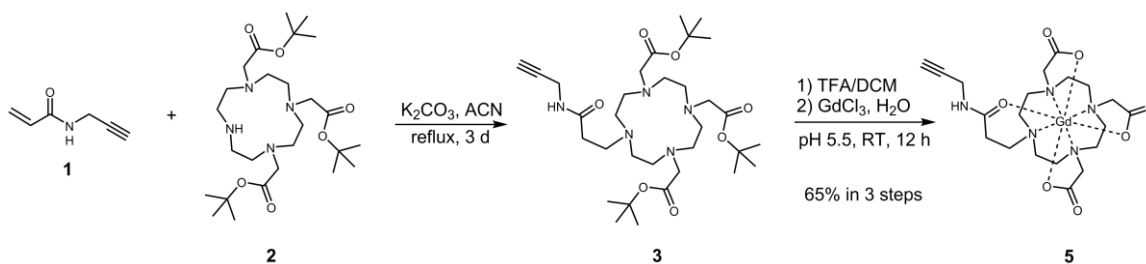

Scheme 2. Chemical synthesis of τ_m -optimized Gd(III) complex(5). Synthesis of (1) proceeds through reaction of acryloyl chloride and propargylamine (Scheme S1). Conjugation of the propionate arm to *tert*-Butyl DO3A (2) is achieved by 1,4 conjugate addition in ACN over 3 days. Deprotection of the macrocycle (4) in trifluoroacetic acid is followed by metalation by GdCl₃ at pH 5.5 for 12 h and HPLC purification.

ligand based on DO3A was synthesized (Scheme 2). Importantly, a pendant alkyne is present to facilitate conjugation using click chemistry. Linker arm 1 was synthesized from acryloyl chloride and propargylamine in 72% yield. Attachment of 1 to previously synthesized DO3A macrocycle 2 proceeds *via* a 1,4 conjugate addition in the presence of base over 3 days.⁴³ Deprotection of compound 3 in trifluoroacetic acid generates the triacetate ligand 4 (Scheme S3), and metalation followed by reverse phase high pressure liquid chromatography (RP-HPLC) purification resulted in a 65% yield of the Gd(III) complex 1-(N-(prop-2-yn-1-yl)2-oxopropyl)-4,7,10-tris(carboxymethyl)-1,4,7,10-tetraazacyclododecyl-gadolinium(III) (5).

To determine the τ_m of complex **5**, a variable temperature ^{17}O titration was performed. Results were fitted to the SBM equations and a τ_m of 22 ns at 37 °C was observed.³¹ This result represents an improvement of nearly 680 ns from the previously described Gd(III) complex in DNA-Gd^{III}@AuNPs (Figure S1).³¹ The successful optimization of this parameter is particularly significant because in cases where $\tau_m \ll T_1$ (a scenario known as a ‘fast exchange’ regime), inner-sphere water molecules account for the greatest contribution to r_1 by efficiently transmitting the relaxation enhancement of the Gd(III) coordinated water molecules to the bulk.³⁰

To verify the number of inner-sphere water molecules (q), the Eu(III) analog of complex **5** was synthesized (complex **6**, Scheme S4). Using the modified Horrocks’ method, equimolar solutions of **6** in water and D₂O were prepared and luminescence lifetimes of each solution were recorded and fitted, resulting in a $q = 1.1 \pm 0.1$ (Figure S2).^{44, 45}

Synthesis and Characterization of DNA-Gd@stars Synthesis of Gd(III) labeled DNA began by incorporation of a C6 amino modified deoxythymidine (dT) nucleotide into five positions along the 24-mer poly dT oligonucleotide sequence (Scheme 1, Scheme S6). The 3’-thiolated 24-mer (5x amino modified) poly dT - Cy3 - 5’ was reacted with azidobutyrate N-hydroxy succinimide ester in the presence of base to install the azide functionality. Finally, complex **5** was covalently attached to the poly azido DNA *via* a Cu(I) catalyzed 1,3 dipolar cycloaddition (CuAAC, or ‘click’ chemistry). The successful synthesis of the 3’ thiolated Gd(III) poly dT-Cy3-5’ oligonucleotide was subsequently confirmed by matrix assisted laser desorption ionization mass spectrometry (MALDI-MS).

Synthesis of nanostars was performed by the reduction of chloroauric acid by 4-(2-Hydroxyethyl)piperazine-1-ethanesulfonic acid (HEPES) buffer.^{46, 47} DNA-Gd@Star conjugates were synthesized by salt aging purified Gd(III)-DNA in water over three days (Scheme 1). Purified particles appear dark green due to the plasmon resonance at 800 nm and are stable in water for >12 weeks when stored at 4 °C.

Transmission electron micrographs (TEM) (Figure 1, inset) show that DNA-Gd@stars contain multiple (up to 8) branches, have an average tip-to-tip diameter of *ca.* 50 nm, and an approximate volume of $1.6 \times 10^4 \text{ nm}^3$ (supporting information). Significantly, individual particles possess regions of positive (branch tips) and negative curvatures (between branches), and flat regions (branch length) (Figure 1). Upon functionalization with Gd(III)-DNA, the average

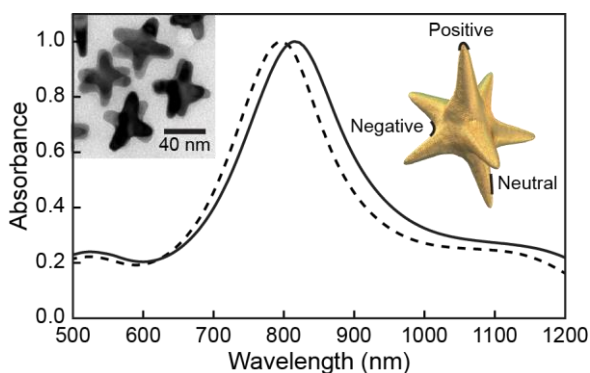


Figure 1. Absorbance spectra of nanostars (dashed line) and DNA-Gd@stars (solid line) indicate an 18 nm resonance shift after functionalization. Insets are a TEM image of nanostar and scheme indicating nanostar curvature.

hydrodynamic diameter of nanostars increased from $38.8 \pm 0.1 \text{ nm}$ to $63.0 \pm 0.7 \text{ nm}$ (Table S1) and the maximum surface plasmon absorbance wavelength shifted from 800 nm to 818 nm, indicating that the Gd(III)-DNA was successfully conjugated to the nanostar surface and that colloidal stability is maintained (Figure 1). A critical feature for biological applications, the Gd(III)-DNA coating was effective in stabilizing DNA-Gd@stars under a range of salt (0-450

mM NaCl) and pH (pH 3-11) conditions, and in cell culture media (DMEM + 10% FBS) (Figure S4).

To quantify DNA loading, inductively coupled plasma mass spectrometry (ICP-MS) was used to determine the ratio of Gd(III) to Au. DNA-Gd@stars contained 1990 ± 450 Gd(III) complexes per nanostar, corresponding to 398 ± 90 DNA strands per nanostar. This loading represents greater than a three-fold increase in Gd(III) payload relative to DNA-Gd@spheres due to larger particle size, and is comparable in Gd(III) payload relative to the DNA-Gd@spheres_{40nm} (Table S1). The number of gold atoms per particle is approximated by calculating the nanostar volume in >180 particles using TEM and the density of bulk gold (supporting information).

Molar Relaxivity of DNA-Gd@stars To assess the performance of DNA-Gd@stars, the r_1 of the nanoconjugates was determined by taking the slope of the linear plot of $1/T_1$ vs. Gd(III) concentration (Table S3, Figure S5). The surprising value of $54.7 \text{ mM}^{-1} \text{ s}^{-1}$ per Gd(III) in water at 60 MHz and 37 °C was obtained (the average of multiple batches, Table S2). This value is among the highest reported for a Gd(III)-nanoconjugate (for one inner-sphere water molecule, or $q = 1$) and is in the same range as supramolecular- or protein-bound Gd(III) complexes. Similarly high values of r_1 are observed for Gd(III) conjugated to viral capsids, non-covalently bound to human serum albumin (MS-325), or entrapped in apoferritin.^{15, 48, 49}

To investigate the source of such high r_1 values, the relaxivities of the unconjugated Gd(III) complex (Scheme 2), and DNA-bound Gd(III) were examined separately. The r_1 of complex **5**, and unconjugated Gd(III)-DNA were found to be $3.8 \text{ mM}^{-1} \text{ s}^{-1}$ and $9.5 \text{ mM}^{-1} \text{ s}^{-1}$, respectively (Table 1). Though incrementally higher than equivalent values using the previously described Gd(III) complex (**7**), the relaxivities observed were unremarkable.²² In order to validate the high relaxivity of the assembled nanostar constructs, five replicate batches of DNA-Gd@stars were

synthesized and measured, showing relaxivities between 42.3 and 69.1 mM⁻¹ s⁻¹ (37 °C, 60 MHz), and Gd(III) loading between 1231 and 2473 Gd(III) per particle (Table S2). For the purpose of comparison, spherical conjugates were synthesized using the same Gd(III)-DNA (DNA-Gd@spheres and DNA-Gd@spheres_{40nm}) (Figure S3).¹ When examined at low field strength (where differences in r_1 are most evident, here 1.41 T),³⁰ r_1 relaxivities measured only 14.6 mM⁻¹ s⁻¹ and 16.8 mM⁻¹ s⁻¹, respectively. Taking the product of the particle loading (Table S1) and high r_1 per Gd(III), DNA-Gd@stars exhibit a three-fold greater relaxivity per particle relative to DNA-Gd@spheres_{40nm}, despite comparable Gd(III) payload. These results (Table 1) indicate that the shape, *not the size* of the nanostar conjugates, is the cause of the large r_1 in this system.

Table 1. Relaxivities of DNA-Gd@stars and DNA-Gd@spheres at 60 and 300 MHz. ‘Ionic’ r_1 refers to the contribution of each individual Gd(III) complex to proton relaxation, whereas ‘particle’ describes the product of each particle’s payload and ionic r_1 .

	r_1 relaxivity ($\text{mM}^{-1} \text{s}^{-1}$)	
	60 MHz ^a	300 MHz ^b
ProHance	3.0 ^c	4.0
Complex 5	3.8	NM
Gd(III)-DNA	9.5	NM
DNA-Gd@stars /ionic	54.7	9.4
DNA-Gd@stars /particle	108850	19345
DNA-Gd@spheres /ionic	14.6	5.8
DNA-Gd@spheres /particle	8230	3270
DNA-Gd@spheres _{40nm} /ionic	16.8	NM
DNA-Gd@spheres _{40nm} /particle	34520	NM

^ameasured at 37 °C in water plus 0.01% tween 20. ^bmeasured at 25 °C in water plus 0.01% tween20 ^cas previously reported⁵⁰ NM = not measured

High-Field r_1 of DNA-Gd@stars As the demand for improved contrast-to-noise ratios and image resolution continues to grow, research has trended toward the use of higher field strength MR instruments.³ As a consequence, Gd(III) contrast agent performance at high-field is becoming increasingly important. To demonstrate the ability of DNA-Gd@stars to increase T_1 contrast at high magnetic fields, solution phantoms were acquired on a 7 T Bruker PharmaScan (300 MHz). DNA-Gd@star samples were imaged at varying concentrations, and the T_1 relaxation times of each tube were used to calculate high-field relaxivity. DNA-Gd@stars generated an r_1 of $9.4 \text{ mM}^{-1} \text{ s}^{-1}$, while the r_1 of the commercially available CA, ProHance, was only $4.0 \text{ mM}^{-1} \text{ s}^{-1}$ at 25 °C in water (Figure 2). Solutions of ProHance at the concentrations examined (equimolar in Gd(III) with DNA-Gd@stars) showed contrast enhancement indistinguishable from the water control (Figure 2, Figure S12).

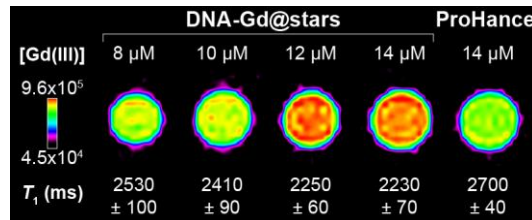


Figure 2. High-field MR solution phantoms (25 °C, 7 T) of aqueous solutions of DNA-Gd@stars vs. equimolar concentrations of the clinical CA ProHance (standardized to [Gd(III)]). Approximate diameter of capillary tubes=1 mm. Calibration bar is signal intensity.

NMRD Acquisition For a detailed mechanistic investigation into the cause of the very high relaxivities observed, DNA-Gd@stars and DNA-Gd@spheres were subjected to a nuclear magnetic relaxation dispersion (NMRD) analysis. Due to the small difference in r_1 observed between the different sizes of spherical nanoconjugates at 1.41 T, only the 15-nm DNA-Gd@spheres (which most closely resemble the DNA-gold nanoparticle conjugates in literature) were taken forward for NMRD comparison to DNA-Gd@stars.^{1, 22-25, 51-53} Using this technique, proton T_1 relaxation rates of water are observed in the presence of paramagnetic species across a range of magnetic field strengths. With the acquired data, proton relaxivity profiles are created and fitted using SBM theory or other more recently developed approaches such as the modified Florence model.⁵⁴⁻⁵⁶ The analysis of relaxivity profiles provides a means of extracting valuable mechanistic information, including dynamic parameters such as τ_r and τ_m .^{31, 57-59}

The NMRD profiles of the nanostar and 15-nm spherical nanoparticle conjugates were measured at 25 °C and 37 °C in water. After acquisition, spectra were normalized to the Gd(III) concentration, and the resulting relaxivity profiles were analyzed using the modified Florence model and the independently measured values for τ_m and q (Figure 3).^{54, 55, 60, 61}

NMRD Analysis The NMRD profile of DNA-Gd@stars shows a maximum relaxivity peak of $98 \text{ mM}^{-1} \text{ s}^{-1}$ at 25°C , centered at approximately 32 MHz. This *very large* value exceeds the theoretical limit that can be calculated with SBM theory, including that calculated with the modified Florence model, when only one water molecule is coordinated to the Gd(III) ion (Figure S13).³⁰

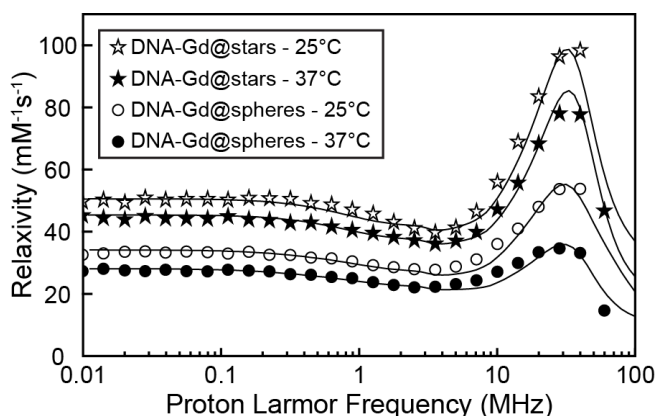


Figure 3. NMRD profiles for water solutions of DNA-Gd@stars and DNA-Gd@spheres. Best fit parameters for the profiles are reported in Table S12 and S13.

As a consequence, this profile could not be reproduced by constraining $q = 1$. Even when including contributions from the outer coordination sphere (water molecules freely diffusing up to a distance of closest approach of 3.6 \AA), the data could not be fit.^{62, 63} Allowing the analysis to consider a value of $q > 1$ was observed to provide the best fit of the NMRD data. This is a physically unlikely scenario, however, because neither the attachment of the Gd(III) complex to the DNA, nor conjugation to the gold nanoparticle is expected to affect the coordination environment of the Gd(III) and affect q .⁵⁰ To rationalize these results, the analysis was reformulated so that $q = 1$, but was made to include both the previously added outer-sphere contributions and significant contributions from second coordination sphere water molecules.^{64, 65} In this analysis, the τ_r of the DNA-Gd@stars is assumed to be larger than T_{1e} and τ_m ($\tau_r \geq 1 \text{ \mu s}$), and thus beyond the ability to affect r_1 significantly. As a result, four second-sphere water

molecules ($q^{SS} = 4$) at a Gd(III)-proton distance of 3.5 Å were required to fit the data successfully. This interpretation required an *exceptionally* large contribution to r_1 from the second-sphere water molecules, which is unusual because in most Gd(III) complexes this contribution is <10% of total r_1 .³⁰ Due to the covariance between q^{SS} and the Gd(III)-proton distance, larger values of q^{SS} are feasible for even larger proton distances.

By definition, the magnitude of second-sphere effects on r_1 is determined by the number of second-sphere water protons, their distance from and residency lifetimes adjacent to the metal center. In most cases, the second-sphere water molecule lifetimes (τ_m^{SS}) are sufficiently short that their contributions to the bulk paramagnetic relaxivity is small, and therefore these effects are accounted for by combining the second-sphere contribution with the outer-sphere relaxation (when their residence times adjacent to the metal are at or near the diffusional residence time). In order to obtain the large contribution from the second-sphere water molecules in the DNA-Gd@stars, τ_m^{SS} is requisitely assigned relatively long values (0.1-1 ns) compared to diffusion (tens of picoseconds). Based on this analysis, we hypothesize that the shape of the DNA-Gd@stars provides a unique, hydrophilic microenvironment where an extended network of transiently associated second-sphere water molecules can reside adjacent to the Gd(III). Many recent examples of nanoconjugate CAs appear to support this hypothesis, though in many cases we find that it is not described explicitly.^{15, 19, 48, 49}

While seldom investigated in mechanistic detail, nanoconjugate CAs that exhibit unusually high r_1 relaxivities often mention the chemical environment of the Gd(III) as a possible explanation. In particular, for CAs that bear extended hydrophilic polymer or protein surfaces, the chemical environment surrounding the lanthanide center is believed to slow water diffusion in the second-sphere of the Gd(III) complexes.^{15, 19, 37, 48, 49} The result of this hydrogen bonding-

rich environment is that each metal center has incrementally longer contact with second-sphere water molecules. In extensive work to study the effects of second-sphere relaxivity (r_1^{SS}), chelates of Gd(III) were synthesized using pendant phosphate groups.^{64, 66, 67} Importantly, Gd(III) complexes were presented wherein the inner-sphere water was displaced by steric crowding ($q = 0$), which allowed for direct experimental determination of second- and outer-sphere relaxivities compared to $q = 1$ controls. In further work, $q = 0$ chelates of Gd(III) were bound to serum albumin (in order to lengthen τ_r and thereby optimize r_1), and could achieve second- and outer-sphere relaxivities as high as $12 \text{ mM}^{-1} \text{ s}^{-1}$ at 20 MHz and 25 °C. This work showed that using pendant hydrogen bonding functional groups and an adjacent hydrophilic protein surface could facilitate contributions from the second-sphere that are quite significant.⁶⁸

The precedent studies and our current results suggest that a sizable contribution to r_1 must be provided by second-sphere water molecules present in the dense monolayer of DNA on the surface of DNA-Gd@stars. This sterically crowded, hydrogen bonding-rich environment likely plays a major role in helping to slow the diffusion of passing water molecules in the proximity of the Gd(III).

Investigating r_1^{SS} in DNA-Gd@stars For additional evidence to support the second-sphere relaxivity hypothesis, the NMRD profile was examined for detailed information about the on-particle water exchange dynamics by observing the change in relaxivities with respect to temperature. A decrease in r_1 with increasing temperature is observed in the DNA-Gd@stars, in agreement with the ‘fast exchange’ behavior of inner-sphere water molecules observed in the exchange dynamics of **5**.⁶⁹ Formally, fast exchange behavior is manifest by a decrease in τ_c with increasing temperature. From the NMRD fit, the T_{1e} at very low fields increases with increasing temperature and is about 0.5-1 ns, whereas τ_r is maintained at values larger than tens of

nanoseconds. Therefore, we conclude that the decrease in r_1 with increasing temperature is the result of a faster τ_m .

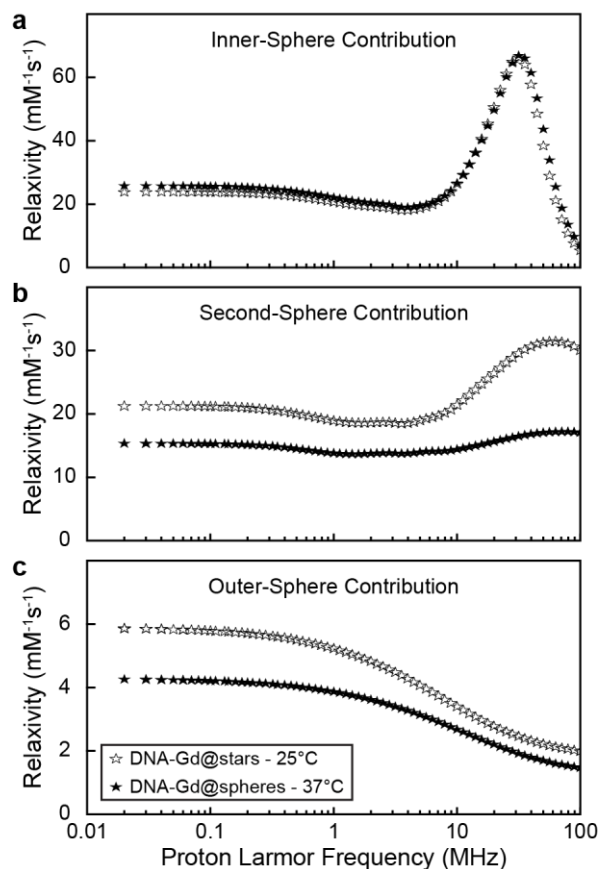


Figure 4. Simulated deconvolution of DNA-Gd@stars NMRD profiles into component inner- (a), second- (b) and outer-sphere (c) contributions.

In the NMRD fit, the τ_m was fixed to the previously measured values of 39 ns and 22 ns at 25 °C and 37 °C, respectively. The τ_m^{SS} , however, was left to vary. After fitting, the respective inner-, second- and outer-sphere components of r_1 were plotted and analyzed (Figure 4, Table S11). The results showed that the contribution to r_1 from inner-sphere water molecules was almost independent of temperature, despite the nearly two-fold difference in τ_m between the two temperatures. This indicates that the inner-sphere residency time of coordinated water molecules is not the major determinant of τ_c for the dipole-dipole interaction with the Gd(III).

The τ_m^{SS} values calculated from the NMRD fitting were 0.6 ns and 0.3 ns at temperatures of 25 °C and 37 °C (Table S12), and were found to be the predominant cause of the observed decrease in r_1 between the two temperatures (Figure 4b). This change in τ_m^{SS} represents a two-fold change in the exchange rate between the two temperatures, which is similar in magnitude, but on a time scale nearly two orders of magnitude more rapidly, than the inner-sphere exchange rate (although still slow compared to diffusion). Here, we show that the 44% decrease of r_1 with increasing temperature is largely determined by second-sphere water proton residence lifetimes (Table S11). Specifically, at the clinically relevant field strength of 1.5 T (64 MHz), we find an r_1^{SS} of 31.5 mM⁻¹ s⁻¹ of a total 54.8 mM⁻¹ s⁻¹ at 25 °C, and 17.2 mM⁻¹ s⁻¹ of a total 44.3 mM⁻¹ s⁻¹ at 37 °C (57.4% and 38.8% second-sphere contribution, respectively). For this reason, the r_1^{SS} contribution provides a significant increase in the overall performance of the DNA-Gd@stars relative to other Gd(III) nanoconjugates.

NMRD Analysis of DNA-Gd@spheres To verify that the irregular shape of the nanostars is responsible for the high relaxivities observed, the 15-nm DNA-Gd@spheres synthesized using the same Gd(III)-DNA were studied by NMRD (Figure 3). The spherical particles show a similar behavior with respect to temperature (a fast exchange regime), but generate a considerably lower r_1 . The NMRD profile from the spherical nanoparticle system could be fitted using $q = 1$, where most of r_1 can be attributed to inner-sphere relaxation (with only minor contributions from the second- and outer-sphere). The temperature-dependent difference in r_1 is attributed to the less optimal reorientation times resulting from increased local mobility, τ_{fast} (Table S13).^{15, 70} The effects of local mobility were not included in the analysis of the DNA-Gd@stars because this treatment would result in even larger r_1^{SS} (due to faster Gd(III) reorientation times, and thus decreased inner-sphere relaxivity, r_1^{IS}).

By comparing the NMRD data for the DNA-Gd@spheres and the DNA-Gd@stars, we observe that even without the large second-sphere contribution to r_1 , the Gd(III) nanostar conjugates generate an r_1^{IS} of $66.9 \text{ mM}^{-1} \text{ s}^{-1}$ at 32 MHz and 37 °C. This value is approximately twice the total r_1 of the DNA-Gd@sphere conjugates at the same field and temperature. This suggests that the shape of DNA-Gd@stars provides a unique environment capable of delivering high relaxivities even in the absence of r_1^{SS} . Furthermore, when comparing the r_1 of the 15-nm DNA-Gd@spheres with that of the 40-nm equivalent at 1.41T (64 MHz), only a minor improvement was observed (Table 1). We believe that this evidence further supports our hypothesis that the *particle shape* is a critical factor for the high performance of the DNA-Gd@stars.

DNA-Gd@star Cell Uptake and Biocompatibility Due to the impressive r_1 observed for DNA-Gd@stars, and the precedent that other oligonucleotide-coated nanoparticles are able to efficiently enter cells without transfection agents, we believe DNA-Gd@stars are promising CAs for applications such as cellular tracking or cancer diagnosis.^{22, 51} For this reason, we investigated the ability of DNA-Gd@stars to deliver Gd(III) to cancer cells *in vitro*. To examine if DNA-Gd@stars maintain the desired cellular uptake and biocompatibility of small spherical nanoconjugate platforms that are well characterized in the literature, we did a comparison with the 15-nm DNA-Gd@spheres.^{22-24, 68} We also compare DNA-Gd@stars to a commercially available CA (ProHance).

In cellular uptake studies, pancreatic cancer cells (PANC-1) were incubated with increasing Gd(III) concentrations of DNA-Gd@stars, DNA-Gd@spheres, or ProHance for 24 hours. To remove non-internalized CAs, cells were washed 3 times with ice-cold PBS prior to trypsinization, then washed an additional 2 times by centrifugation and resuspension in fresh

buffer. Finally, cells were counted and digested in a 1:1 mixture of HNO₃ and HCl for metals analysis using ICP-MS. Results indicated that the Gd(III) payload delivered per cell by incubation with DNA-Gd@stars was 50 times higher than incubation with ProHance, and *ca.* 1.4 times higher than that by DNA-Gd@spheres (Figure 5b).

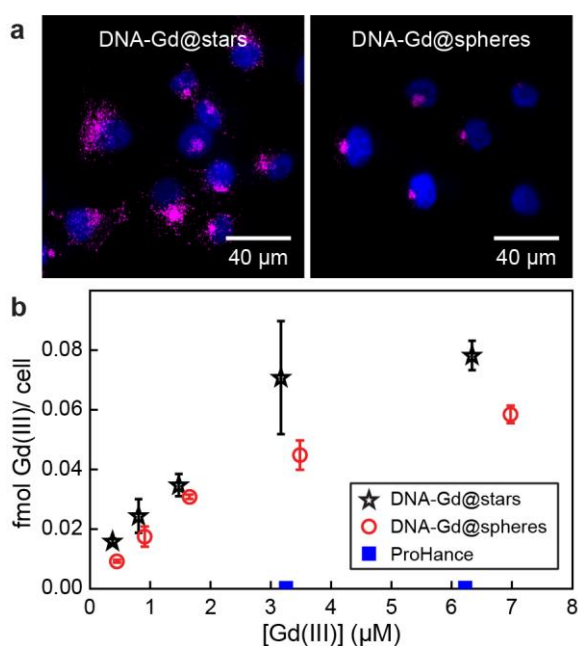


Figure 5. (a) Confocal images of DNA-Gd@stars and DNA-Gd@spheres ([Gd(III)]=1.5 μM) taken up by PANC-1 cells. Magenta signal represents Cy3-labeled nanoconjugates imaged under identical microscope conditions (without post-processing) and blue signal represents DAPI stained nuclei. (b) Femtomoles of Gd(III) taken up per cell, quantified by ICP-MS.

Previous reports suggest that between 10⁷-10⁹ Gd(III) ions per cell are required to produce detectable contrast in MRI.²² Thus, DNA-Gd@stars delivered Gd(III) payloads that are expected to generate visible contrast using only low-micromolar incubation concentrations (4.5×10⁷ ions per cell with 6 μM Gd(III) incubation concentration, Batch 5 in Table S2). To check for detectable contrast in cell pellet images, PANC-1 cells were incubated with 0, 3 and 6 μM Gd(III) concentrations of DNA-Gd@stars or the commercial CA ProHance for 24 hr. After washing, cell pellets were added to glass capillary tubes and imaged using a Bruker PharmaScan 7T (Figure S14). Analysis of the resulting images confirmed that the *T*₁ of cells incubated with

DNA-Gd@stars were reduced compared to untreated cells and ProHance ($p < 0.02$). These results highlight that in addition to significantly improving r_1 , DNA-Gd@stars efficiently penetrate cells, enabling detectable contrast in cell pellets using as low as 3 μM Gd(III) incubation concentrations.

Confocal fluorescence micrographs were obtained to visualize the uptake and intracellular localization of DNA-Gd@stars and 15-nm DNA-Gd@spheres in PANC-1 cells (24-h incubation, $[\text{Gd(III)}] = 1.5 \mu\text{M}$). The fluorescence from the Cy3-labeled conjugates were obtained under identical microscope conditions, and were not post-processed, for a more accurate visual comparison (Figure 5a). The Cy3 signal of DNA-Gd@stars appears brighter than that of DNA-Gd@spheres, consistent with the quantitative results gathered by ICP-MS.

We attribute the difference in Gd(III) delivery primarily to greater loading as a result of the higher surface area of the gold nanostars compared to the 15-nm spheres. Interestingly, we noticed a difference in the intracellular localization of the two conjugates. DNA-Gd@stars are distributed through the cytoplasm of the cells, while the DNA-Gd@spheres are primarily localized in the perinuclear region, consistent with the previous generation of DNA-Gd^{III}@AuNPs.²² Although beyond the scope of the current study, this result suggests that differences may exist in the uptake or intracellular trafficking (e.g., endosomal-lysosomal pathway) behavior between the star- and spherical-shaped conjugates and warrants further investigation into the effects of the nanostar shape and size on cellular interactions.

Finally, the toxicity of the DNA-Gd@stars and DNA-Gd@spheres conjugates was evaluated using the CellTiter 96 MTS assay. After a 24 hour incubation up to 6 μM Gd(III) concentrations, no cytotoxicity was observed for either conjugate (Figure S15). Considering the exceptionally high r_1 of DNA-Gd@stars, these *in vitro* results demonstrate that this platform is an effective and

biocompatible CA for cellular MR imaging that requires only low- μM Gd(III) incubation concentrations to generate detectable image contrast.

CONCLUSION

The use of MRI for longitudinal, *in vivo* studies presents clear advantages over competing modalities for its safety, soft tissue contrast and limitless depth penetration. As a result, the investigation of new Gd(III) CAs has been of great interest to the research community. Herein we report a new class of gold nanoconjugates that exhibit exceptionally high relaxivities at both low *and* high field strengths. Using NMRD analysis we have shown that nanoparticle shape and surface curvature affect the organization of conjugated DNAs on the particle surface and that this plays a meaningful role in sequestration of water molecules in the proximity of the Gd(III) complexes. Upon incubation with pancreatic cancer cells, DNA-Gd@stars improve Gd(III) delivery and maintain biocompatibility when compared side-by-side with DNA-Gd@spheres and commercial CAs. These results indicate the strategic value of designing the Gd(III) chelate into a dense, hydrophilic microenvironment to facilitate longer access to second-sphere water molecules, and thereby generate contrast enhancement greater than can be achieved using small molecule CAs alone. These results will facilitate future nanoconjugate CA development by consideration of particle shape and surface chemistry as vital parameters in the proton relaxation mechanism of Gd(III) based agents.

MATERIALS AND METHODS

Chemical Synthesis and Characterization All reagents and solvents were purchased from Sigma-Aldrich unless otherwise noted. All chemical synthesis was performed under ambient conditions unless described explicitly. Chemical characterization was achieved using a Varian 500 MHz NMR and a Bruker AutoFlex III MALDI spectrometer. Ligand and Gd(III) complex purification was performed using a Varian Prostar 500 HPLC using a Waters 4.6×250 mm $5 \mu\text{m}$ Atlantis C18 column and mobile phases of Millipore water, 0.05% trifluoroacetic acid in Millipore water, and acetonitrile. Nanoparticle characterization was performed on JOEL 1230 and Hitachi HD7700 TEMs. UV/Vis/NIR spectra of colloidal solutions were collected on a LAMBDA 1050 spectrophotometer (Perkin Elmer). DLS and

zeta-potential measurements were done with a Brookhaven ZetaPals zeta potential and particle size analyzer.

Oligonucleotides were synthesized on solid phase controlled pore glass beads (CPGs) by standard techniques on a MerMade automated synthesizer. All reagents and protected 3' thiol modifier CPGs and C6 amino modifier dT modified bases were purchased from Glen Research (Sterling, Va). Oligonucleotides were deprotected from the solid phase using AMA conditions [(1:1 methylamine:ammonium hydroxide (*sat.*))] for one hour. Purification of oligonucleotides was performed using reverse phase high performance liquid chromatography (HPLC) on a Varian HPLC using a mobile phase consisting of 30mM triethyl ammonium acetate buffer pH 7 (TEAA) and acetonitrile (ACN). Separation was achieved using a gradient of 75% Acetonitrile over 45minutes, as monitored by backbone and Cy3 wavelengths at 254 and 546 nm respectively. Purified oligonucleotides were lyophilized and stored at -20 °C until particle synthesis. Inorganic Gd(III) complex **5** was synthesized using standard organic chemistry techniques.

ICP-MS was performed on either a computer-controlled (Plasmalab software) Thermo (Thermo Fisher Scientific, Waltham, MA) PQ ExCell ICP-MS equipped with a CETAC 500 autosampler or a computer-controlled (Plasmalab software) Thermo X series II ICP-MS equipped with an ESI (Omaha, NE, USA) SC-2 autosampler.

Synthesis of Gold Nanostars: Gold nanostars were synthesized by reducing chloroauric acid in 4-(2-Hydroxyethyl)piperazine-1-ethanesulfonic acid (HEPES buffer) to create biocompatible, surfactant-free gold nanoparticles.⁴⁶ Specifically, chloroauric acid (0.2 mM final concentration) was added to HEPES buffer (100 mM), shaken for 1 minute, then left to grow for at least 30 min. The resonance wavelength of the nanostars was measured using UV/vis spectroscopy.

Synthesis of Spherical Gold Nanoparticles: Gold nanoparticles were synthesized by published procedures. The plasmon resonance wavelength was observed by UV/Vis spectroscopy and size was confirmed by DLS and TEM (Figure S3b). 40-nm unconjugated gold colloids were purchased from Ted Pella and characterized by DLS and TEM (Figure S3c).

Relaxivity (r_1): A stock solution of DNA-Gd@star conjugates was made (700 uL). This stock was serially diluted four times for a total of five solutions. Solutions were heated to 37 °C and two hundred uL of each concentration was placed into a Bruker minispec mq60 NMR spectrometer (60 MHz) for measurement of T_1 relaxation time. Data were collected using an inversion recovery pulse sequence using 4 averages, a 15s repetition time and 10 data points. The remaining volumes of each solution were utilized for ICP analysis of [Gd(III)]. The inverse of the longitudinal relaxation time ($1/T_1$, s^{-1}) was plotted versus the Gd(III) concentration (mM). By applying a linear fit to this data, the slope that is generated is defined as the relaxivity of the agent ($mM^{-1} s^{-1}$). Relaxivities of DNA-Gd@spheres, Gd(III)-DNA and complex **5** were collected by the analogous procedure.

Metals Analysis by ICP-MS: Quantitation of metal concentration was performed by acid digestion of nanoconjugate samples, followed by ICP-MS analysis. Gadolinium and gold analyses were prepared by different dilution factors such that were within the range of the selected standard concentrations. Specifically, Gd analyses were digested by addition of 20 ul of nanoconjugate sample into 120 ul of 1:1 concentrated nitric acid: concentrated hydrochloric acid (TraceSelect Nitric acid, >69% ; TraceSelect HCl, fuming 37%) and mixed thoroughly. Au analyses were made by addition of 5 uL of nanoconjugate sample to 500 uL of 1:1 HNO₃:HCl as above, and mixed thoroughly. Millipore water and multi-element internal standard (CLISS-1, Spex Certiprep, Metuchen, NJ, USA) containing 6Li, Sc, Y, In, Ho, Bi were added to produce a solution of 2% nitric acid (v/v), 2% HCl (v/v) and 5.0 ng/mL internal standard up to a total sample volume of 3 mL (Gd) and 10 mL (Au) after 20-fold dilution of original aliquot. Individual Au and Gd elemental standards were prepared at 0, 0.78125, 1.5625, 3.125, 6.25, 12.5, 25.0, 50.0, 100,

and 200 ng/mL concentrations with 2% nitric acid (v/v), 2% HCl (v/v) and 5.0 ng/mL internal standards up to a total sample volume of 5 mL. Each sample was acquired using 1 survey run (10 sweeps) and 3 main (peak jumping) runs (100 sweeps). The isotopes selected were ^{197}Au , $^{156,157}\text{Gd}$ and ^{115}In , ^{165}Ho , and ^{209}Bi (as internal standards for data interpolation and machine stability).

NMRD Data: Water proton relaxation rates of solutions containing nanostar and nanosphere conjugates were measured from 0.01 to 40 MHz proton Larmor frequency using a fast field cycling Stellar relaxometer. The relaxivity profiles of the DNA-Gd@stars and DNA-Gd@spheres were obtained after the subtraction of the diamagnetic 24-mer poly dT gold nanoconjugate equivalents and normalized to 1mM Gd(III) concentration.

Cell Culture: Pancreatic cancer cells (PANC-1, ATCC) were maintained in DMEM medium (Gibco) supplemented with 10% fetal bovine serum (FBS) (Invitrogen). Cells were grown in T25 flasks (VWR) at 37 °C and 5% CO₂.

Quantification of Gd(III) Uptake in Cells: 30,000 PANC-1 cells were seeded in each well of a 24-well plate overnight. The cell culture media was replaced with varying concentrations (in triplicate) of DNA-Gd@stars, DNA-Gd@spheres, or ProHance suspended in the serum-containing growth medium and incubated for 24 h at 37 °C. The CA-doped media was removed and the wells were washed 3x with ice-cold PBS followed by trypsinization. The cells were then washed twice more *via* centrifugation (900 xg, 5 min) and resuspending in PBS. Finally, cells were counted with a hemacytometer then digested in 120 ul of 1:1 concentrated nitric acid: concentrated hydrochloric acid overnight. ICP-MS samples and standards were prepared as described above.

Confocal Imaging of Cy3-Labeled DNA-Gd@stars and DNA-Gd@spheres: PANC-1 cells were grown on collagen coated coverslips then incubated for 24 hrs with 1.5 μM [Gd(III)] of DNA-Gd@stars and DNA-Gd@spheres in growth medium. Cells were washed 3x with ice cold PBS, fixed in 4% paraformaldehyde, and mounted on a glass slide with a drop of ProLong Gold antifade reagent (Invitrogen). The fixed samples were imaged on an inverted Zeiss 510 confocal microscope using a 40x water immersion objective and a 533 nm HeNe laser to excite the Cy3-labeled nanoconjugates. All microscope parameters (pinhole size, gain, offset, laser intensity) were kept constant between imaging DNA-Gd@star and DNA-Gd@sphere samples. The Cy3 channel was not post-processed. The blue DAPI channel was processed (despeckle, Gaussian blur, adjust min/max) with FIJI to enhance visualization of the cell nuclei.

Conflict of Interest: The authors declare no competing financial interest.

Acknowledgment: We gratefully acknowledge support by NIH Grant R01EB005866, the National Cancer Institute Center for Cancer Nanotechnology Excellence initiative at Northwestern University Award No. U54CA151880, and the National Institutes of Health (NIH) Director's Pioneer Award DP1OD003899. We acknowledge Government support under FA9550-11-C-0028 and awarded by the Department of Defense, Air Force Office of Scientific Research, National Defense Science and Engineering Graduate (NDSEG) Fellowship, 32 CFR 168a (K. Culver). NMRD acquisition and analysis was performed at the Magnetic Resonance Center (CERM) at the University of Florence, and was supported by the Ente Cassa di Risparmio di Firenze, MIUR PRIN 2012SK7ASN, EC Contract pNMR No. 317127. The Center for Advanced Molecular Imaging (CAMI) provided MR imaging and the Quantitative Bio-elemental Imaging Center (QBIC) at Northwestern provided confocal microscopy and ICP-MS analysis respectively and were supported by National Science Foundation CHE-9810378/005 and NASA Ames Research Center NNA06CB93G. Compound purification and characterization was performed at the Integrated Molecular Structure Education and Research Center (IMSERC). M. Rotz

would like to thank the Mirkin Lab at Northwestern for the gracious use of lab equipment for DNA synthesis and purification, and for the supply of helpful advice over many years. The authors would also like to thank Raymond C. Lee for synthesis of the gold nanostar stock solutions. TEM imaging work was performed at the Northwestern University Biological Imaging Facility (BIF), and was generously supported by the NU Office for Research. Electron microscopy was performed on a JEOL 3200 FETEM purchased with the support of NCCR 1S10RR025092. UV-vis spectroscopic measurements were performed at the NU Keck Biophysics Facility supported by Cancer Center Support Grant (NCI CA060553). This work made use of the EPIC facility (NUANCE Center-Northwestern University), which has received support from the MRSEC program (NSF DMR-1121262) at the Materials Research Center; the Nanoscale Science and Engineering Center (NSF EEC-0647560) at the International Institute for Nanotechnology; and the State of Illinois, through the International Institute for Nanotechnology. Cell viability assays were carried out in the High Throughput Analysis (HTA) Laboratory at Northwestern University. The authors would like to thank Northwestern Visualization and the NUI Academic & Research Technologies for preparation of the nanoconjugate graphics herein.

Supporting Information Available: Details of synthesis, purification and chemical characterization of small molecules, nanoparticle synthesis, characterization, raw data for calculations of τ_m and q NMRD fitting parameters, additional TEM images, relaxometry measurements, ICP-MS analysis, nanoconjugate colloidal stability, cell pellet images and additional confocal images are available. This material is available free of charge *via* the Internet at <http://pubs.acs.org>.

REFERENCES

1. Hurst, S. J.; Lytton-Jean, A. K. R.; Mirkin, C. A. Maximizing DNA Loading on a Range of Gold Nanoparticle Sizes. *Anal. Chem.* **2006**, *78*, 8313-8318.
2. Dempsey, M. F.; Condon, B.; Hadley, D. M. Mri Safety Review. *Seminars in Ultrasound, CT and MRI* **2002**, *23*, 392-401.
3. Willinek, W. A.; Schild, H. H. Clinical Advantages of 3.0T Mri over 1.5T. *European Journal of Radiology* **2008**, *65*, 2-14.
4. Shellock, F. G.; Spinazzi, A. Mri Safety Update 2008: Part 2, Screening Patients for Mri. *Am. J. Roentgenol.* **2008**, *191*, 1140-1149.
5. Shellock, F. G.; Spinazzi, A. Mri Safety Update 2008: Part 1, Mri Contrast Agents and Nephrogenic Systemic Fibrosis. *Am. J. Roentgenol.* **2008**, *191*, 1129-1139.
6. Caravan, P.; Ellison, J. J.; McMurry, T. J.; Lauffer, R. B. Gadolinium(III) Chelates as Mri Contrast Agents: Structure, Dynamics, and Applications. *Chem. Rev.* **1999**, *99*, 2293-2352.
7. Solomon, I. Relaxation Processes in a System of Two Spins. *Physical Review* **1955**, *99*, 559-565.
8. Bloembergen, N.; Morgan, L. O. Proton Relaxation Times in Paramagnetic Solutions. Effects of Electron Spin Relaxation. *J. Chem. Phys.* **1961**, *34*, 842-850.
9. Aime, S.; Calabi, L.; Cavallotti, C.; Gianolio, E.; Giovenzana, G. B.; Losi, P.; Maiocchi, A.; Palmisano, G.; Sisti, M. [Gd-Aazta]-: A New Structural Entry for an Improved Generation of Mri Contrast Agents. *Inorg. Chem.* **2004**, *43*, 7588-7590.
10. Cohen, S. M.; Xu, J.; Radkov, E.; Raymond, K. N.; Botta, M.; Barge, A.; Aime, S. Syntheses and Relaxation Properties of Mixed Gadolinium Hydroxypyridinonate Mri Contrast Agents. *Inorg. Chem.* **2000**, *39*, 5747-5756.
11. Villaraza, A. J.; Bumb, A.; Brechbiel, M. W. Macromolecules, Dendrimers, and Nanomaterials in Magnetic Resonance Imaging: The Interplay between Size, Function, and Pharmacokinetics. *Chem. Rev.* **2010**, *110*, 2921-2959.
12. Michael, A. B.; Xin, Y.; Nicole, F. S. Engineering Gd-Loaded Nanoparticles to Enhance Mri Sensitivity Via T1 Shortening. *Nanotechnology* **2013**, *24*, 462001.

13. Prasuhn, J. D. E.; Yeh, R. M.; Obenaus, A.; Manchester, M.; Finn, M. G. Viral Mri Contrast Agents: Coordination of Gd by Native Virions and Attachment of Gd Complexes by Azide-Alkyne Cycloaddition. *Chem. Commun.* **2007**, 1269-1271.
14. Garimella, P. D.; Datta, A.; Romanini, D. W.; Raymond, K. N.; Francis, M. B. Multivalent, High-Relaxivity Mri Contrast Agents Using Rigid Cysteine-Reactive Gadolinium Complexes. *J. Am. Chem. Soc.* **2011**, *133*, 14704-14709.
15. Caravan, P.; Parigi, G.; Chasse, J. M.; Cloutier, N. J.; Ellison, J. J.; Lauffer, R. B.; Luchinat, C.; McDermid, S. A.; Spiller, M.; McMurry, T. J. Albumin Binding, Relaxivity, and Water Exchange Kinetics of the Diastereoisomers of Ms-325, a Gadolinium(III)-Based Magnetic Resonance Angiography Contrast Agent. *Inorg. Chem.* **2007**, *46*, 6632-6639.
16. Manus, L. M.; Mastarone, D. J.; Waters, E. A.; Zhang, X.-Q.; Schultz-Sikma, E. A.; MacRenaris, K. W.; Ho, D.; Meade, T. J. Gd(III)-Nanodiamond Conjugates for Mri Contrast Enhancement. *Nano Lett.* **2009**, *10*, 484-489.
17. Kielar, F.; Tei, L.; Terreno, E.; Botta, M. Large Relaxivity Enhancement of Paramagnetic Lipid Nanoparticles by Restricting the Local Motions of the Gd(III) Chelates. *J. Am. Chem. Soc.* **2010**, *132*, 7836-7837.
18. Lee, S.-M.; Song, Y.; Hong, B. J.; MacRenaris, K. W.; Mastarone, D. J.; O'Halloran, T. V.; Meade, T. J.; Nguyen, S. T. Modular Polymer-Caged Nanobins as a Theranostic Platform with Enhanced Magnetic Resonance Relaxivity and Ph-Responsive Drug Release. *Angew. Chem.* **2010**, *122*, 10156-10160.
19. Courant, T.; Roullin, V. G.; Cadiou, C.; Callewaert, M.; Andry, M. C.; Portefaix, C.; Hoeffel, C.; de Goltstein, M. C.; Port, M.; Laurent, S., *et al.* Hydrogels Incorporating GdDOTA: Towards Highly Efficient Dual T1/T2 Mri Contrast Agents. *Angew. Chem. Int. Ed.* **2012**, *51*, 9119-9122.
20. Endres, P. J.; Paunesku, T.; Vogt, S.; Meade, T. J.; Woloschak, G. E. DNA-TiO₂ Nanoconjugates Labeled with Magnetic Resonance Contrast Agents. *J. Am. Chem. Soc.* **2007**, *129*, 15760-15761.
21. Heffern, M. C.; Matosziuk, L. M.; Meade, T. J. Lanthanide Probes for Bioresponsive Imaging. *Chem. Rev.* **2013**, *114*, 4496-4539.
22. Song, Y.; Xu, X.; MacRenaris, K. W.; Zhang, X.-Q.; Mirkin, C. A.; Meade, T. J. Multimodal Gadolinium-Enriched DNA-Gold Nanoparticle Conjugates for Cellular Imaging. *Angew. Chem. Int. Ed.* **2009**, *48*, 9143-9147.
23. Rosi, N. L.; Giljohann, D. A.; Thaxton, C. S.; Lytton-Jean, A. K. R.; Han, M. S.; Mirkin, C. A. Oligonucleotide-Modified Gold Nanoparticles for Intracellular Gene Regulation. *Science* **2006**, *312*, 1027-1030.
24. Giljohann, D. A.; Seferos, D. S.; Patel, P. C.; Millstone, J. E.; Rosi, N. L.; Mirkin, C. A. Oligonucleotide Loading Determines Cellular Uptake of DNA-Modified Gold Nanoparticles. *Nano Lett.* **2007**, *7*, 3818-3821.
25. Seferos, D. S.; Prigodich, A. E.; Giljohann, D. A.; Patel, P. C.; Mirkin, C. A. Polyvalent DNA Nanoparticle Conjugates Stabilize Nucleic Acids. *Nano Lett.* **2008**, *9*, 308-311.
26. Helm, L.; Merbach, A. E. Water Exchange on Metal Ions: Experiments and Simulations. *Coord. Chem. Rev.* **1999**, *187*, 151-181.
27. Manus, L. M.; Strauch, R. C.; Hung, A. H.; Eckermann, A. L.; Meade, T. J. Analytical Methods for Characterizing Magnetic Resonance Probes. *Anal. Chem.* **2012**, *84*, 6278-6287.
28. Micskei, K.; Helm, L.; Brucher, E.; Merbach, A. E. Oxygen-17 Nmr Study of Water Exchange on Gadolinium Polyaminopolyacetates [Gd(Dtpa)(H₂O)]²⁻ and [Gd(Dota)(H₂O)]⁻ Related to Nmr Imaging. *Inorg. Chem.* **1993**, *32*, 3844-3850.
29. Aime, S.; Barge, A.; Borel, A.; Botta, M.; Chemerisov, S.; Merbach, A. E.; Müller, U.; Pubanz, D. A Multinuclear Nmr Study on the Structure and Dynamics of Lanthanide(III) Complexes of the Poly(Amino Carboxylate) Egta⁴⁻ in Aqueous Solution. *Inorg. Chem.* **1997**, *36*, 5104-5112.
30. Caravan, P.; Farrar, C. T.; Frullano, L.; Uppal, R. Influence of Molecular Parameters and Increasing Magnetic Field Strength on Relaxivity of Gadolinium- and Manganese-Based T1 Contrast Agents. *Contrast Media Mol. Imaging* **2009**, *4*, 89-100.

31. Toth, E.; Helm, L.; Merbach, A. E., Relaxivity of Gadolinium (Iii) Complexes: Theory and Mechanism. In *Chemistry of Contrast Agents in Medical Magnetic Resonance Imaging*, Toth, E.; Merbach, A. E., Eds. John Wiley & Sons Ltd.: 2001; pp 45-119.
32. Clarkson, R. B.; Smirnov, A. I.; Smirnova, T. I.; Belford, R. L., Multi-Frequency and High-Frequency Epr Methods in Contrast Agent Research: Examples from Gd³⁺ Chelates. In *Chemistry of Contrast Agents in Medical Magnetic Resonance Imaging*, Toth, E.; Merbach, A. E., Eds. John Wiley & Sons Ltd.: 2001; pp 383-415.
33. Ruloff, R.; Toth, E.; Scopelliti, R.; Tripier, R.; Handel, H.; Merbach, A. E. Accelerating Water Exchange for Gdiii Chelates by Steric Compression around the Water Binding Site. *Chem. Commun.* **2002**, 2630-2631.
34. Laus, S.; Ruloff, R.; Tóth, É.; Merbach, A. E. Gdiii Complexes with Fast Water Exchange and High Thermodynamic Stability: Potential Building Blocks for High-Relaxivity Mri Contrast Agents. *Chem. Eur. J.* **2003**, *9*, 3555-3566.
35. Jaszberenyi, Z.; Sour, A.; Toth, E.; Benmelouka, M.; Merbach, A. E. Fine-Tuning Water Exchange on Gdiii Poly(Amino Carboxylates) by Modulation of Steric Crowding. *Dalton Trans.* **2005**, 2713-2719.
36. Tóth, É.; Pubanz, D.; Vauthey, S.; Helm, L.; Merbach, A. E. The Role of Water Exchange in Attaining Maximum Relaxivities for Dendrimeric Mri Contrast Agents. *Chem. Eur. J.* **1996**, *2*, 1607-1615.
37. Strauch, R. C.; Mastarone, D. J.; Sukerkar, P. A.; Song, Y.; Ipsaro, J. J.; Meade, T. J. Reporter Protein-Targeted Probes for Magnetic Resonance Imaging. *J. Am. Chem. Soc.* **2011**, *133*, 16346-16349.
38. Moriggi, L. c.; Cannizzo, C.; Dumas, E.; Mayer, C. d. R.; Ulianov, A.; Helm, L. Gold Nanoparticles Functionalized with Gadolinium Chelates as High-Relaxivity Mri Contrast Agents. *J. Am. Chem. Soc.* **2009**, *131*, 10828-10829.
39. Walker, D. A.; Leitsch, E. K.; Nap, R. J.; Szleifer, I.; Grzybowski, B. A. Geometric Curvature Controls the Chemical Patchiness and Self-Assembly of Nanoparticles. *Nat Nano* **2013**, *8*, 676-681.
40. Ferreira, M. F.; Mousavi, B.; Ferreira, P. M.; Martins, C. I. O.; Helm, L.; Martins, J. A.; Geraldes, C. F. G. C. Gold Nanoparticles Functionalised with Stable, Fast Water Exchanging Gd³⁺ Chelates as High Relaxivity Contrast Agents for Mri. *Dalton Trans.* **2012**, *41*, 5472-5475.
41. Graepi, N.; Hugh Powell, D.; Laurency, G.; Zékány, L.; Merbach, A. Coordination Equilibria and Water Exchange Kinetics of Lanthanide(Iii) Propylenediaminetetraacetates and Other Magnetic Resonance Imaging Related Complexes. *Inorg. Chim. Acta* **1995**, *235*, 311-326.
42. Tei, L.; Gugliotta, G.; Baranyai, Z.; Botta, M. A New Bifunctional Gdiii Complex of Enhanced Efficacy for Mr-Molecular Imaging Applications. *Dalton Trans.* **2009**, 9712-9714.
43. Axelsson, O.; Olsson, A. Synthesis of Cyclen Derivatives. WO/2006/112723, 2006.
44. Supkowski, R. M.; Horrocks Jr, W. D. On the Determination of the Number of Water Molecules, Q, Coordinated to Europium(Iii) Ions in Solution from Luminescence Decay Lifetimes. *Inorg. Chim. Acta* **2002**, *340*, 44-48.
45. Beeby, A.; M. Clarkson, I.; S. Dickins, R.; Faulkner, S.; Parker, D.; Royle, L.; S. de Sousa, A.; A. Gareth Williams, J.; Woods, M. Non-Radiative Deactivation of the Excited States of Europium, Terbium and Ytterbium Complexes by Proximate Energy-Matched Oh, Nh and Ch Oscillators: An Improved Luminescence Method for Establishing Solution Hydration States. *Journal of the Chemical Society, Perkin Transactions 2* **1999**, 493-504.
46. Xie, J.; Lee, J. Y.; Wang, D. I. C. Seedless, Surfactantless, High-Yield Synthesis of Branched Gold Nanocrystals in Hepes Buffer Solution. *Chem. Mater.* **2007**, *19*, 2823-2830.
47. Dam, D. H. M.; Lee, J. H.; Sisco, P. N.; Co, D. T.; Zhang, M.; Wasielewski, M. R.; Odom, T. W. Direct Observation of Nanoparticle–Cancer Cell Nucleus Interactions. *ACS Nano* **2012**, *6*, 3318-3326.
48. Min, J.; Jung, H.; Shin, H.-H.; Cho, G.; Cho, H.; Kang, S. Implementation of P22 Viral Capsids as Intravascular Magnetic Resonance T1 Contrast Conjugates Via Site-Selective Attachment of Gd(Iii)-Chelating Agents. *Biomacromolecules* **2013**, *14*, 2332-2339.

49. Aime, S.; Frullano, L.; Geninatti Crich, S. Compartmentalization of a Gadolinium Complex in the Apoferritin Cavity: A Route to Obtain High Relaxivity Contrast Agents for Magnetic Resonance Imaging. *Angew. Chem. Int. Ed.* **2002**, *41*, 1017-1019.
50. Mastarone, D. J.; Harrison, V. S. R.; Eckermann, A. L.; Parigi, G.; Luchinat, C.; Meade, T. J. A Modular System for the Synthesis of Multiplexed Magnetic Resonance Probes. *J. Am. Chem. Soc.* **2011**, *133*, 5329-5337.
51. Patel, P. C.; Giljohann, D. A.; Daniel, W. L.; Zheng, D.; Prigodich, A. E.; Mirkin, C. A. Scavenger Receptors Mediate Cellular Uptake of Polyvalent Oligonucleotide-Functionalized Gold Nanoparticles. *Bioconjugate Chem.* **2010**, *21*, 2250-2256.
52. Prigodich, A. E.; Lee, O.-S.; Daniel, W. L.; Seferos, D. S.; Schatz, G. C.; Mirkin, C. A. Tailoring DNA Structure to Increase Target Hybridization Kinetics on Surfaces. *J. Am. Chem. Soc.* **2010**, *132*, 10638-10641.
53. Jensen, S. A.; Day, E. S.; Ko, C. H.; Hurley, L. A.; Luciano, J. P.; Kouri, F. M.; Merkel, T. J.; Luthi, A. J.; Patel, P. C.; Cutler, J. I., *et al.* Spherical Nucleic Acid Nanoparticle Conjugates as an RNAi-Based Therapy for Glioblastoma. *Science Translational Medicine* **2013**, *5*, 209ra152.
54. Bertini, I.; Galas, O.; Luchinat, C.; Parigi, G. A Computer Program for the Calculation of Paramagnetic Enhancements of Nuclear-Relaxation Rates in Slowly Rotating Systems. *Journal of Magnetic Resonance, Series A* **1995**, *113*, 151-158.
55. Bertini, I.; Kowalewski, J.; Luchinat, C.; Nilsson, T.; Parigi, G. Nuclear Spin Relaxation in Paramagnetic Complexes of S=1: Electron Spin Relaxation Effects. *J. Chem. Phys.* **1999**, *111*, 5795-5807.
56. Kowalewski, J.; Luchinat, C.; Nilsson, T.; Parigi, G. Nuclear Spin Relaxation in Paramagnetic Systems: Electron Spin Relaxation Effects under near-Redfield Limit Conditions and Beyond. *J. Phys. Chem. A* **2002**, *106*, 7376-7382.
57. Bertini, I.; Luchinat, C.; Parigi, G., 1h Nmr Profiles of Paramagnetic Complexes and Metalloproteins. In *Adv. Inorg. Chem.*, Academic Press: 2005; Vol. Volume 57, pp 105-172.
58. Preslar, A. T.; Parigi, G.; McClendon, M. T.; Sefick, S. S.; Moyer, T. J.; Haney, C. R.; Waters, E. A.; MacRenaris, K. W.; Luchinat, C.; Stupp, S. I., *et al.* Gd(III)-Labeled Peptide Nanofibers for Reporting on Biomaterial Localization in Vivo. *ACS Nano* **2014**, *8*, 7325-7332.
59. Hung, A. H.; Duch, M. C.; Parigi, G.; Rotz, M. W.; Manus, L. M.; Mastarone, D. J.; Dam, K. T.; Gits, C. C.; MacRenaris, K. W.; Luchinat, C., *et al.* Mechanisms of Gadographene-Mediated Proton Spin Relaxation. *The Journal of Physical Chemistry C* **2013**, *117*, 16263-16273.
60. Lauffer, R. B. Paramagnetic Metal Complexes as Water Proton Relaxation Agents for Nmr Imaging: Theory and Design. *Chem. Rev.* **1987**, *87*, 901-927.
61. Helm, L. Relaxivity in Paramagnetic Systems: Theory and Mechanisms. *Prog. Nucl. Magn. Reson. Spectrosc.* **2006**, *49*, 45-64.
62. Hwang, L. P.; Freed, J. H. Dynamic Effects of Pair Correlation Functions on Spin Relaxation by Translational Diffusion in Liquids. *J. Chem. Phys.* **1975**, *63*, 4017-4025.
63. Freed, J. H. Dynamic Effects of Pair Correlation Functions on Spin Relaxation by Translational Diffusion in Liquids. ii. Finite Jumps and Independent T1 Processes. *J. Chem. Phys.* **1978**, *68*, 4034-4037.
64. Botta, M. Second Coordination Sphere Water Molecules and Relaxivity of Gadolinium(III) Complexes: Implications for Mri Contrast Agents. *Eur. J. Inorg. Chem.* **2000**, *2000*, 399-407.
65. Bertini, I.; Fragai, M.; Luchinat, C.; Parigi, G. Solvent 1h Nmr Study of Hexaquochochromium(III): Inferences on Hydration and Electron Relaxation. *Inorg. Chem.* **2001**, *40*, 4030-4035.
66. Geraldes, C. F. G. C.; Brown, R. D.; Cacheris, W. P.; Koenig, S. H.; Sherry, A. D.; Spiller, M. Evaluation of Polyaza Macrocyclic Methylene Phosphonate Chelates of Gd³⁺ Ions as Mri Contrast Agents. *Magn. Reson. Med.* **1989**, *9*, 94-104.
67. Aime, S.; Botta, M.; Terreno, E.; Anelli, P. L.; Uggeri, F. Gd(Dotp)⁵⁻ Outer-Sphere Relaxation Enhancement Promoted by Nitrogen Bases. *Magn. Reson. Med.* **1993**, *30*, 583-591.

68. Aime, S.; S. Batsanov, A.; Botta, M.; S. Dickins, R.; Faulkner, S.; E. Foster, C.; Harrison, A.; A. K. Howard, J.; M. Moloney, J.; J. Norman, T., *et al.* Nuclear Magnetic Resonance, Luminescence and Structural Studies of Lanthanide Complexes with Octadentate Macrocyclic Ligands Bearing Benzylphosphinate Groups. *J. Chem. Soc., Dalton Trans.* **1997**, 3623-3636.
69. Aime, S.; Botta, M.; Fasano, M.; Terreno, E. Prototropic and Water-Exchange Processes in Aqueous Solutions of Gd(III) Chelates. *Acc. Chem. Res.* **1999**, *32*, 941-949.
70. Alhaique, F.; Bertini, I.; Fragai, M.; Carafa, M.; Luchinat, C.; Parigi, G. Solvent 1h Nmr Study of Biotinylated Paramagnetic Liposomes Containing Gd-Bis-Sda-Dtpa or Gd-Dmpe-Dtpa. *Inorg. Chim. Acta* **2002**, *331*, 151-157.